

QUALIFICATION TEST REPORT
FP-13-50
LARGE TRANSPORT TYPE JET
AIRCRAFT AERODYNAMIC TESTING
OF THE CANDIDATE TYPE I FLUID

Arctica DG RTU
lot # 28

Produced at Tatarstan, Russia

for

ARCTON LTD.
P.O. Box 1079
GO 11, Nizhnekamsk
423570, Tatarstan, Russia

by

Diane Paradis
Marc Mario Tremblay



Laboratoire international
des matériaux antigivre

LIMA  AMIL

Anti-icing Materials
International Laboratory

July 2013

QUALIFICATION

This report presents results of high speed ramp aerodynamic acceptance tests, using Boundary Layer Displacement Thickness (BLDT) values, performed on samples of the candidate Type I fluid **ARCTON LTD. Arctica DG RTU lot # 28**, produced at **Tatarstan, Russia**, evaluated concentrated as received according to the latest revisions of the SAE AMS 1424K specification and AS5900B standard [1-3]. The tests were performed between 0°C and -30.9°C within a $\pm 2^\circ\text{C}$ range, using the flat plate set-up in the Luan Phan refrigerated wind tunnel at the Anti-icing Materials International Laboratory (AMIL) research laboratory. AMIL is independent of fluid manufacturers and was found qualified on September 11, 1997 (reconfirmed September 13, 2012) by the Performance Review Institute according to PRI document AC3001, “audit criteria for compliance to SAE AMS 1424 and AMS 1428”.

On the basis of the acceptance criteria, the candidate Type I fluid ARCTON LTD. Arctica DG RTU lot # 28 qualifies according to AMS 1424K specification for use on large transport type jet aircraft in the following temperature range:

- **above -30.5°C in the case of the Fluid as received.**

Final Fluid Thickness (paragraph 3.5.3.1)

The final fluid thickness, based on an initial thickness of 2000 μm , was measured to be from
76 μm to 229 μm *for all dilutions, therefore below the required 400 μm .*

This fluid is qualified from 2013 July 15, for a four year period.



This page left blank.

TABLE OF CONTENTS

QUALIFICATION	i
LIST OF TABLES	iv
LIST OF FIGURES	iv
LIST OF SYMBOLS.....	v
TEST RESULTS	1
TEST DESCRIPTION.....	19
1. INTRODUCTION.....	21
2. TEST DESCRIPTION	21
2.1 Flat Plate Elimination Test	21
2.2 Measurements.....	23
2.3 Calibration and Acceptance Criteria	23
3. TEST RESULTS	24
3.1 Test Presentation	24
3.2 Calculation of the Calibration and Acceptance Criteria.....	25
3.3 Flat Plate Elimination Tests.....	30
4. REFERENCES	30
ATTACHMENT 1.....	31
ATTACHMENT 2.....	35
ACCREDITATION.....	87

LIST OF TABLES

Table 1 - Fluid Identification.....	3
Table 2 - Apparent Surface Tension, pH and Refractive Index	3
Table 3 - Brookfield Viscosity (mPa·s).....	5
Table 4 - Aerodynamic Performance Test Data: Fluid as received	7
Table 5 - Refractive Index Data and Water Change: Fluid as received	15
Table 6 - Viscosity Measurement Details	24
Table 7 - Dry Test Data	26
Table 8 - Aerodynamic Performance Test Data : Reference Fluid	27
Table 9 - Refractive Index Data and Water Change: Reference Fluid.....	28

LIST OF FIGURES

Figure 1 - Aerodynamic Test Results.....	9
Figure 2 - Fluid Elimination	11
Figure 3 - Relative Humidity.....	13
Figure 4 - Refractive Index versus Water Content.....	17
Figure 5 - FPET Set-up.....	22
Figure 6 - Take-off Ground Acceleration Simulation	22
Figure 7 - Acceptance Criteria	29

LIST OF SYMBOLS

δ_{ave}^*	average Boundary Layer Displacement Thickness (BLDT) over the test section perimeter at cross-section 3 (Figure 5) evaluated by the equation 2 in Attachment 1, (mm)
δ^*	Boundary Layer Displacement Thickness (BLDT) over the test section perimeter at cross-section 3 (Figure 5) evaluated by the equation 3 in Attachment 1 (mm)
AIR	Aerospace Information Report
AMIL	Anti-icing Materials International Laboratory
AMS	Aerospace Material Specification
AS	Aerospace Standard
FE	Fluid Elimination during the test (%)
FP	Flat Plate elimination test identification number
FPC	Flat Plate Calibration test identification number
FPD	Flat Plate elimination test Dry (without fluid)
FPET	Flat Plate Elimination Test
P	Static Pressure as measured by gauges positioned at points # 1, 2 and 3 in the set-up (Figure 5) (mPa)
Rh	Relative humidity (%)
SAE	Society of Automotive Engineers
t	Thickness of the film fluid on the plate (μm)
T_a	Air Temperature as recorded at the top of the cross-section 2 in the set up (Figure 5) ($^{\circ}\text{C}$)
T_f	Fluid Temperature as recorded in the fluid film at the bottom of the cross-section 3 (Figure 5) ($^{\circ}\text{C}$)
UQAC	University of Quebec at Chicoutimi
V	Air Velocity derived from the measurement of the pressure difference $P_1 - P_2$ using the equation (1) in Attachment 1 (m/s)
WC	Water Change (% w/w)

This page left blank.

TEST RESULTS

This page left blank.

Table 1 - Fluid Identification

Company Name	Product	Color	Manufacture Location	Manuf. Date	AMIL Label	Recep. Date
ARCTON LTD.	Arctica DG RTU lot # 28 Fluid as received	Orange	Tatarstan, Russia	April 2013	J162	13-06-10
AMIL	Reference Fluid* lot # 20130610	Colorless	Saguenay, Quebec (Canada)	13-06-10	M114	13-06-10

Table 2 - Apparent Surface Tension, pH and Refractive Index

DEICING FLUID ARCTON LTD.

Arctica DG RTU, lot # 28

Fluid	Apparent Surface Tension (± 0.5)		pH (± 0.1)		Refractive Index (± 0.0002)	
	T (°C)	dynes/cm	T (°C)	Value	T (°C)	Value
<i>J162</i>	22	36.8	22	9.4	20	1.4121
<i>M114</i>	not measured	not measured	not measured	not measured	20	1.4278

* For the reference fluid formulation, refer to AS5900B paragraph 2.1.3 for the high speed ramp tests.

This page left blank.

Table 3 - Brookfield Viscosity (mPa·s)
DEICING FLUID ARCTON LTD.
Arctica DG RTU, lot # 28

Fluid	Temp (°C)	0.3 RPM			6 RPM			30 RPM		
		Viscosity	Accuracy	Spindle #	Viscosity	Accuracy	Spindle #	Viscosity	Accuracy	Spindle #
J162	20	< 20	200	1	10	10	1	10.6	2	1
	0	40	200	1	29	10	1	29.0	2	1
	-10	60	200	1	56	10	1	56.2	2	1
	-20	120	200	1	124	10	1	124.0	2	1
	-30	300	1000	2	285	50	2	283	10	2

Fluid	Temp (°C)	0.3 RPM			6 RPM			30 RPM		
		Viscosity	Accuracy	Spindle #	Viscosity	Accuracy	Spindle #	Viscosity	Accuracy	Spindle #
M114	20	40	200	1	37	10	1	37.0	2	1
	0	160	200	1	154	10	1	154.0	2	1
	-10	460	200	1	451	10	1	450	10	2
	-20	1 400	1000	2	1 365	50	2	1 384	40	3
	-30	3 900	1000	2	3 930	50	2	3 908	40	3

For additional viscosity details, see Table 6.

This page left blank.

Table 4 - Aerodynamic Performance Test Data: Fluid as received

DEICING FLUID ARCTON LTD.

Arctica DG RTU, lot # 28

HIGH SPEED RAMP

TEST CODE	T _a °C	T _f °C	Rh %	t ₀ ⁽¹⁾ μm	t _{end} ⁽²⁾ μm	FE ⁽³⁾ %	WC ⁽⁴⁾ %	V ⁽⁵⁾ m/s	δ* mm
J162A022	-0.3	0.7	94.0	2000	84	95.8	6.77*	66.9	3.59
J162A023	-0.3	0.5	94.6	2000	76	96.2	7.64*	67.2	3.75
J162A024	-0.2	0.5	95.7	1933	84	95.7	8.65*	67.0	3.87
J162C040	-10.8	-10.0	81.2	1933	109	94.4	2.38*	67.1	4.51
J162C041	-10.5	-10.2	83.0	1933	119	93.8	2.13*	66.7	4.57
J162C042	-11.3	-10.6	79.5	1933	119	93.8	2.01*	67.1	4.61
J162E052	-21.0	-21.3	67.1	1867	185	90.1	0.63	67.6	5.76
J162E053	-21.3	-21.3	64.8	1867	170	90.9	0.00	67.2	5.65
J162E054	-21.5	-21.4	64.2	1867	178	90.5	0.25	67.1	5.71
J162G062	-32.6	-30.4	57.2	1800	211	88.3	0.13	66.5	8.22
J162G061	-32.5	-30.8	57.8	1800	196	89.1	0.50	66.6	8.24
J162G063	-32.3	-30.9	59.7	1800	229	87.3	0.25	66.6	8.04

*caution : value outside the ± 2% range

Acceptance Criteria :

D₀ = 8.59 mm D₋₁₀ = 9.30 mm D₋₁₅ = 9.66 mm D₋₂₀ = 10.02 mm

(1) Thickness of the fluid measured at the beginning of the test.

(2) Thickness of the fluid measured at the end of the test.

(3) Fluid Elimination.

(4) Water Change.

(5) Air velocity 30 seconds after the beginning of the test.

This page left blank.

ARCTON LTD.
Arctica DG RTU, lot # 28

High Speed Ramp Test

AMIL 2013-06-27

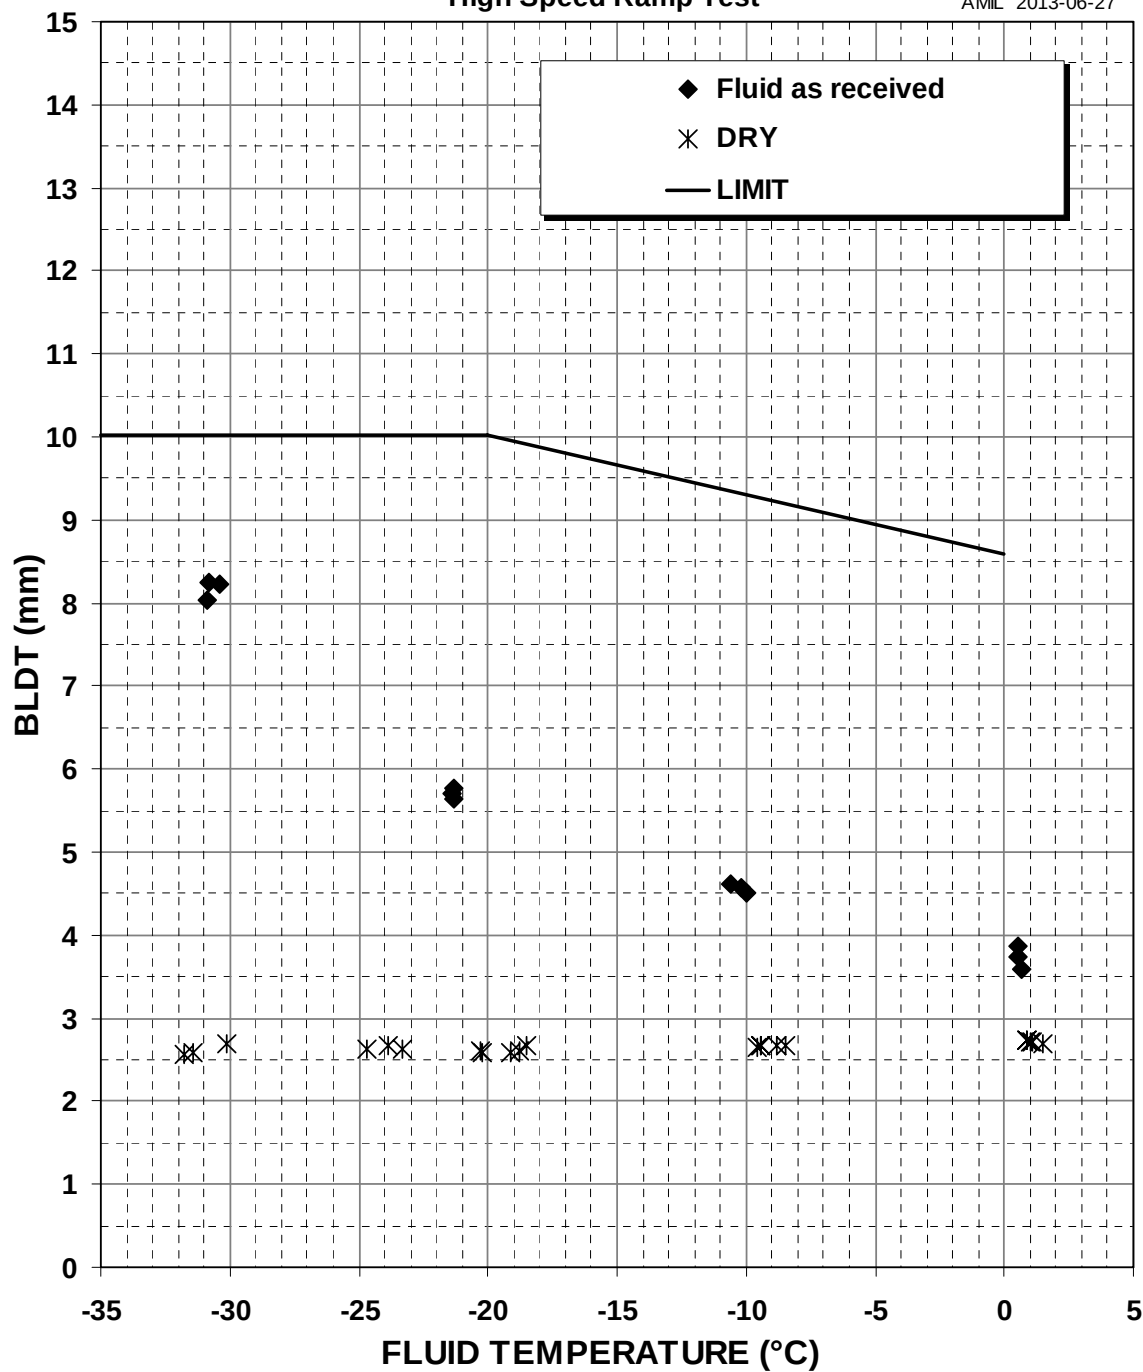


Figure 1 - Aerodynamic Test Results

This page left blank.

ARCTON LTD.
Arctica DG RTU, lot # 28

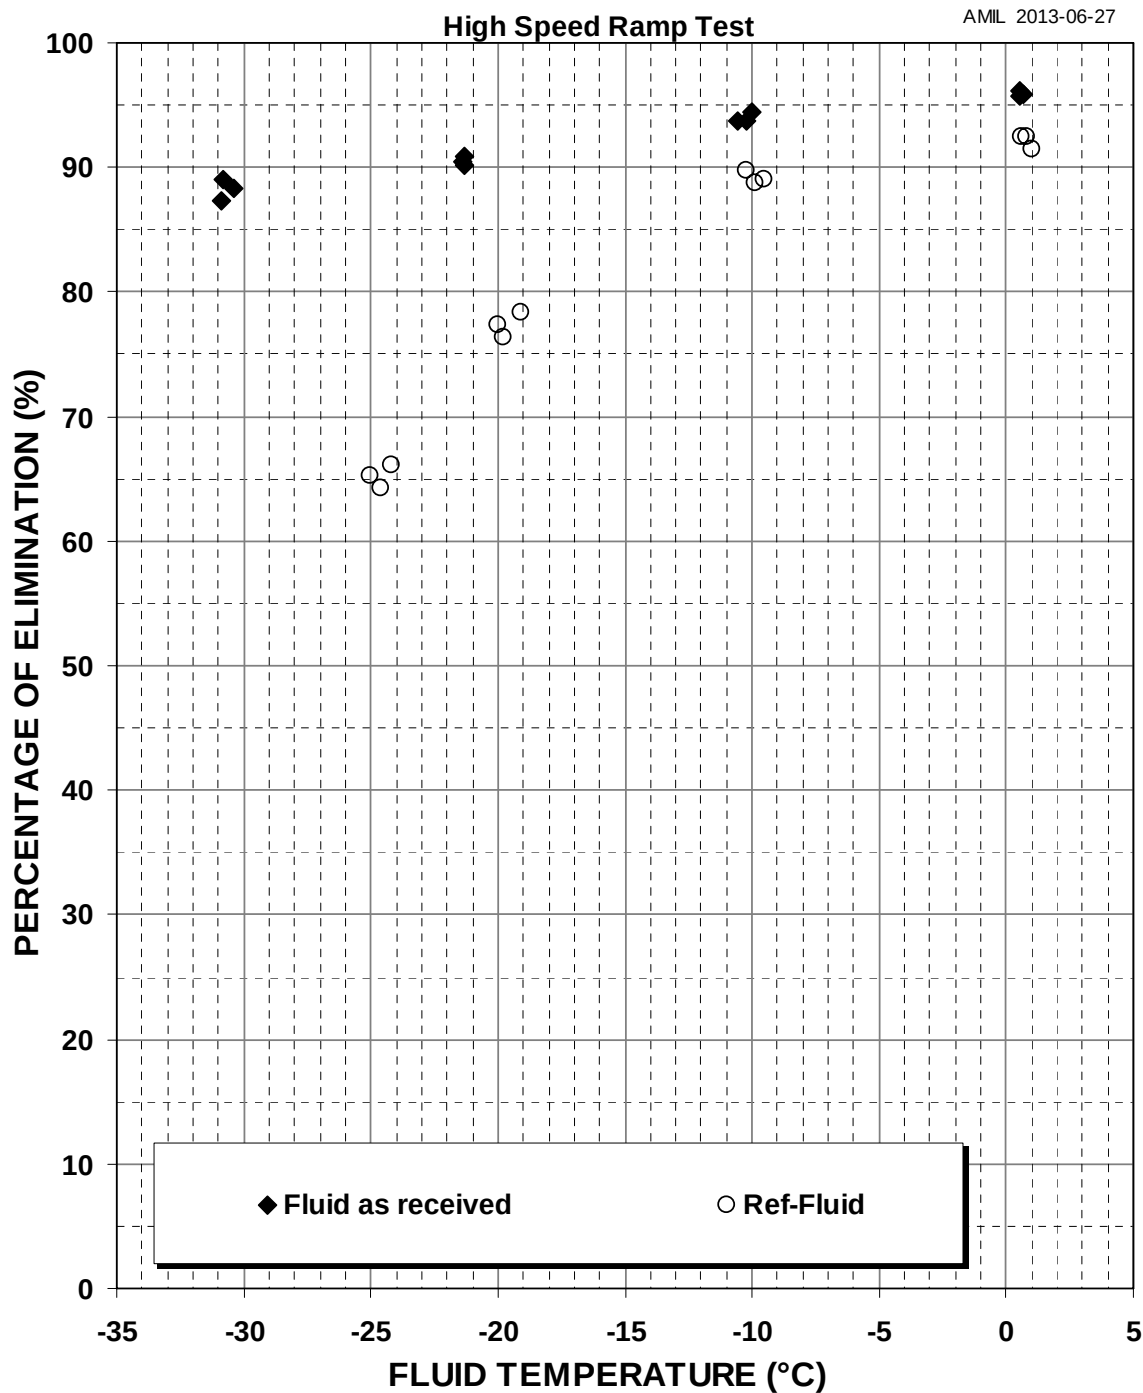


Figure 2 - Fluid Elimination

This page left blank.

ARCTON LTD.

Arctica DG RTU, lot # 28

High Speed Ramp Test

AMIL 2013-06-27

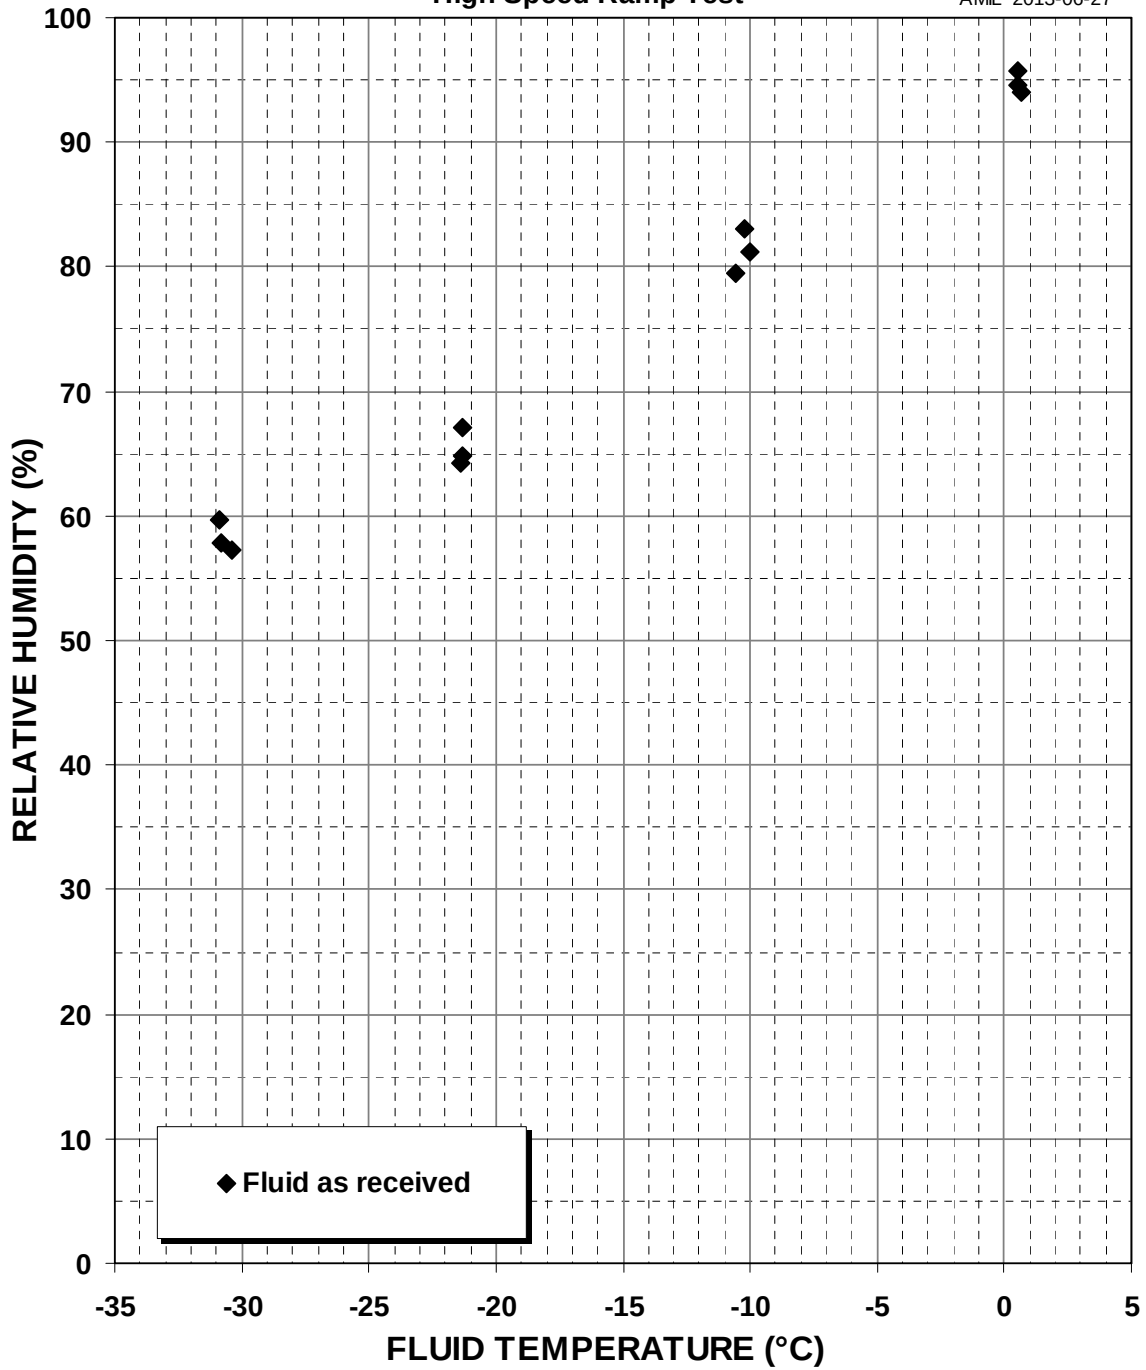


Figure 3 - Relative Humidity

This page left blank.

**Table 5 - Refractive Index Data and Water Change:
Fluid as received**

**DEICING FLUID ARCTON LTD.
Arctica DG RTU, lot # 28**

TEST CODE	RI Initial	RI Final	Δ RI	WC % W/W	Rh %
J162A022	1.4126	1.4072	-0.0054	6.77*	94.0
J162A023	1.4124	1.4063	-0.0061	7.64*	94.6
J162A024	1.4124	1.4055	-0.0069	8.65*	95.7
J162C040	1.4124	1.4105	-0.0019	2.38*	81.2
J162C041	1.4123	1.4106	-0.0017	2.13*	83.0
J162C042	1.4124	1.4108	-0.0016	2.01*	79.5
J162E052	1.4122	1.4117	-0.0005	0.63	67.1
J162E053	1.4117	1.4117	0.0000	0.00	64.8
J162E054	1.4120	1.4118	-0.0002	0.25	64.2
J162G062	1.4123	1.4122	-0.0001	0.13	57.2
J162G061	1.4126	1.4122	-0.0004	0.50	57.8
J162G063	1.4123	1.4121	-0.0002	0.25	59.7

*caution : value outside the $\pm$ 2% range

This page left blank.

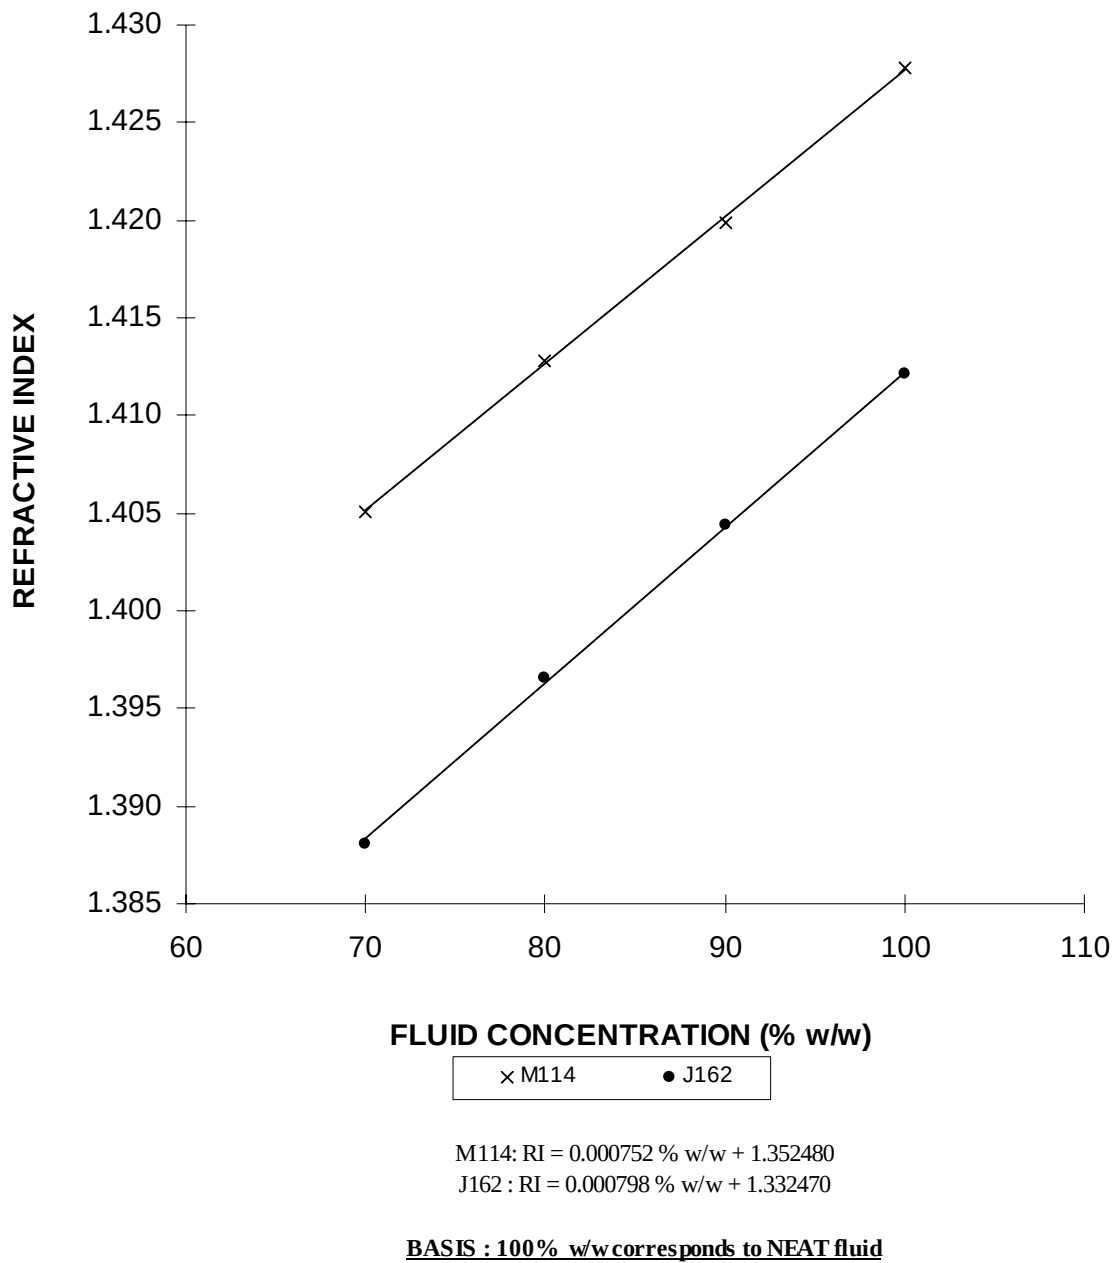


Figure 4 - Refractive Index versus Water Content

This page left blank.

TEST DESCRIPTION

This page left blank.

1. INTRODUCTION

This report details the performance of fluid samples, identified in Table 1, when subjected to the Flat Plate Elimination Test, denoted FPET hereafter. The FPET procedure follows the SAE Aerospace Material Specifications, AMS 1424K [2] and Aerospace Standard AS5900B [3] for deicing fluid on the high speed ramp. The tests were carried out in the Luan Phan refrigerated wind tunnel of the "Anti-icing Materials International Laboratory" (AMIL) at the "Université du Québec à Chicoutimi" (UQAC) [4]. UQAC facility is operated independently from fluid manufacturers and meets the requirements of the aerodynamic acceptance testing standards. It was found qualified on September 11, 1997 (reconfirmed September 13, 2012) by the Performance Review Institute according to PRI document AC3001, "audit criteria for compliance to SAE AMS 1424 and AMS 1428".

2. TEST DESCRIPTION

2.1 Flat Plate Elimination Test

This test is designed to measure the Boundary Layer Displacement Thickness, BLDT, which is related to lift loss [5]. The flat plate set-up consists of a duct inserted in the test section of AMIL refrigerated wind tunnel. In this tunnel, the airflow and the fluid can be maintained at a constant temperature, between $5^{\circ}\text{C} \pm 1^{\circ}\text{C}$ and $-45^{\circ}\text{C} \pm 2^{\circ}\text{C}$. A set-up sketch is given in Figure 5.

The FPET procedure consists in submitting a 2 mm thick layer of deicing product covering the duct floor to an accelerating air flow of 2.6 m/s^2 , simulating a large transport-type aircraft take-off (Figure 6). The BLDT on the flat plate is measured at pressure tap location # 3 (Figure 5), thirty seconds after the beginning of the simulated take-off. A detailed description of this test is presented in AS5900B [3].

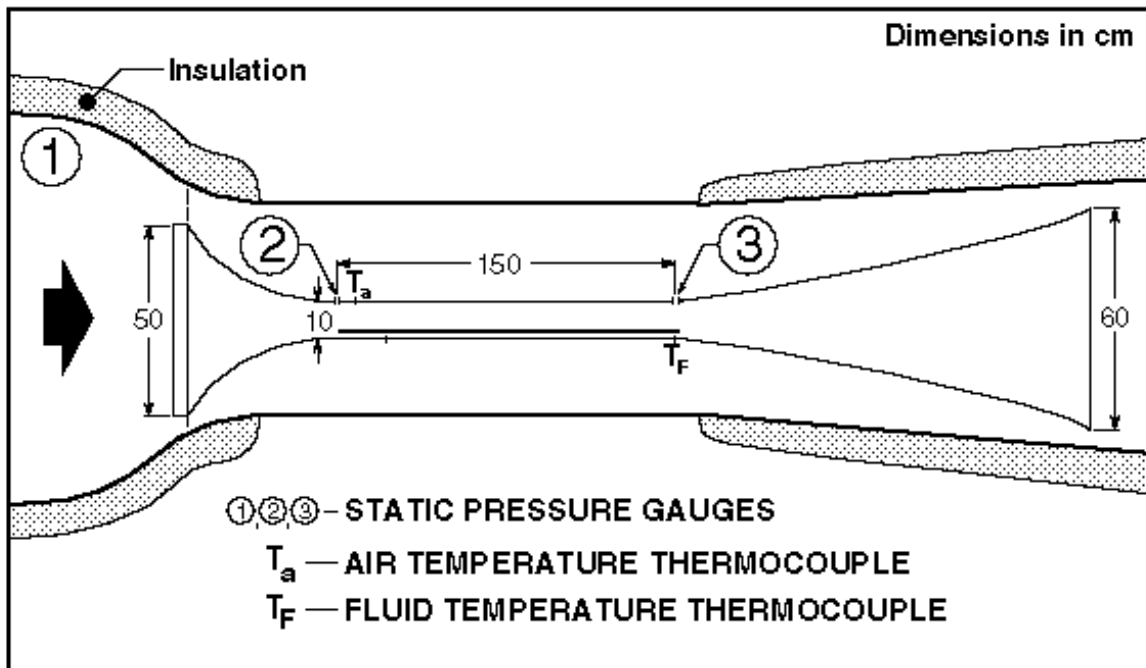


Figure 5 - FPET Set-up

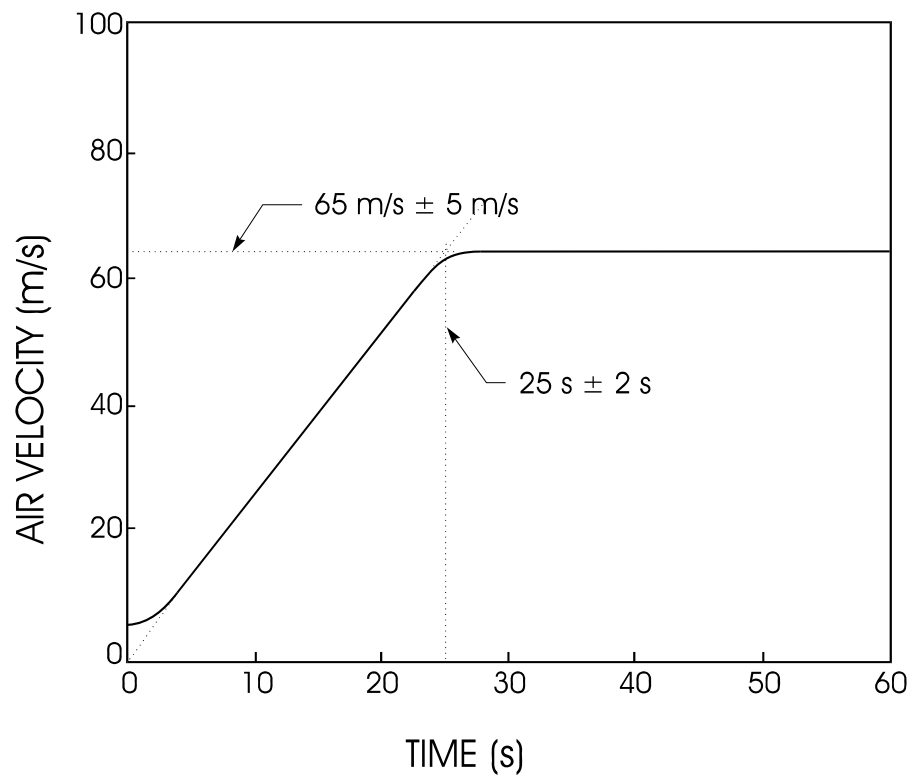


Figure 6 - Take-off Ground Acceleration Simulation

2.2 Measurements

In a FPET, the fluid performance is evaluated from BLDT measurements. The BLDT value used for the fluid evaluation is the average of the BLDT measured between the 27th and the 33rd seconds after the beginning of the test. The starting time ($t = 0$) is evaluated by extrapolating the straight line of the acceleration ramp to the point where $V = 0$ m/s.

In addition, the following parameters are measured:

1. **apparent surface tension at room temperature (dynes/cm)**

Apparent Surface Tension measured with a DuNouy precision tensiometer, CSC Scientific Company Inc., model No. 70535, using a 5.992 cm pulling ring.

2. **pH at room temperature**

pH values measured with a Fisher Accumet pHmeter, Fisher Scientific Company, model 925, using a pHRESH, Flow-On-Demand Epoxy Body Combination pH Electrode, Beckman, model 511110.

3. **refractive index which is used to determine the water change (%)**

Refractive Index measured with a REICHERT AR7 SERIES Refractometer, Reichert, Inc., model AR70.

4. **viscosity at room and test temperatures (mPa . s)**

5. **fluid film thickness (μm) at the beginning and at the end of the FPET to compute fluid elimination (%)**

2.3 Calibration and Acceptance Criteria

The calibration is obtained from dry tests, performed without fluid, and Reference Fluid tests (as described in AS5900B paragraph 2.1.3), for which BLDT results are well documented. The BLDT values obtained from a dry test should be $2.5 \text{ mm} \pm 0.4 \text{ mm}$. For dry and calibration tests, the BLDT values are recorded at four temperatures: 0°C , -10°C , -20°C and -25°C . Reference Fluid BLDT values and dry BLDT values are used to calculate the acceptance criteria required for certification. A candidate fluid is acceptable at a test temperature if none of the independent BLDT measurements is greater than the acceptance criteria. This test temperature is the average of the three lowest temperatures of the acceptable data points.

3. TEST RESULTS

3.1 Test Presentation

The fluid identification is presented in Table 1 and the fluid physical properties in the following tables : Apparent surface tension, pH and refractive index values are given in Table 2 and Brookfield viscosity values in Table 3. FPET results are presented in Table 4. Calibration data from dry tests and tests with the reference fluid are reproduced in Table 7 and Table 8 respectively. Finally, Table 5, presents refractive index data and water change calculations. Figure 4 shows the refractive index as a function of water change. Fluid elimination and relative humidity are presented as a function of test temperature in Figure 2 and Figure 3 respectively.

Table 6 - Viscosity Measurement Details

Fluid Type	Measurement Device	Spindle #	Container Description	Sample Volume (ml)	Rotation Duration (min)		
					0.3 RPM	6 RPM	30 RPM
I	LV	1	600 ml Beaker	600	5	5	5
		2		600	5	5	5
		3		550	5	5	5
		4		550	5	5	5
II	SSA	31	13 R (P)	10	30	5	5
III		34	13 R (P)	10	30	5	5
IV		16	8 R (P)	4.2	30	5	5
		18	13 R (P)	8	30	5	5

The viscometers are calibrated yearly by the accredited laboratory CAN-AM Instruments, Ltd. The NIST traceable calibration certificate is available upon request.

3.2 Calculation of the Calibration and Acceptance Criteria

Calibration tests, as defined in section 2.3, consist of dry tests and tests with the Reference Fluid. The dry test results are presented in Table 7. According to specifications [2], the AMIL system is considered adequately calibrated, since the dry test BLDT value (δ^*) varies within the standard range of $2.5 \text{ mm} \pm 0.4 \text{ mm}$. The Reference Fluid results are presented in Table 8. These results are also in agreement with known values. As mentioned in section 2.3, dry and Reference Fluid BLDT values are used to compute the criteria of acceptance, presented below and in Figure 7. Below -20°C , the acceptance envelope is a constant straight line with a BLDT equal to the value D20. Between -20°C and 0°C , the acceptance envelope is a straight line from D20, at -20°C , to D0, at 0°C . The D20 and D0 are calculated accordingly to the AS5900B standard for the high speed ramp:

Calculation of acceptance level at -20°C:	Calculation of acceptance level at 0°C:
$D20 = \delta_{ref}^* - 0.18 \left(\delta_{ref}^* - \delta_{dry}^* \right)_{-20}$	$D0 = \delta_{ref}^* + 0.71 \left(\delta_{ref}^* - \delta_{dry}^* \right)_0$
$D20 = 11.63 - 0.18 \times (11.63 - 2.66) = 10.02 \text{ mm}$	$D0 = 6.13 + 0.71 \times (6.13 - 2.66) = 8.59 \text{ mm}$

Table 7 - Dry Test Data

TEST CODE	T _a (°C)	T _f (°C)	Rh (%)	V ⁽¹⁾ (m/s)	δ_{dry}^* (mm)
DRY_A280	-0.2	1.5	91.1	65.8	2.70
DRY_A282	-0.4	1.1	92.8	65.5	2.71
DRY_A279	0.6	1.0	93.9	65.9	2.71
DRY_A277	-1.3	0.9	76.8	66.2	2.73
DRY_A278	0.1	0.9	90.2	65.9	2.73
DRY_C292	-10.7	-8.5	79.4	65.7	2.68
DRY_C290	-10.5	-8.8	74.0	66.1	2.67
DRY_C289	-12.1	-9.4	68.6	64.9	2.68
DRY_C291	-10.4	-9.4	75.3	66.0	2.67
DRY_C294	-10.3	-9.6	85.4	66.0	2.64
DRY_E296	-20.7	-18.5	62.2	65.6	2.67
DRY_E295	-21.8	-18.8	61.9	65.9	2.61
DRY_E297	-20.7	-19.1	62.8	66.1	2.59
DRY_E298	-21.3	-20.2	70.2	65.6	2.59
DRY_E300	-21.7	-20.3	65.2	65.0	2.61
DRY_F288	-25.5	-23.3	58.3	66.3	2.63
DRY_F287	-25.4	-23.9	59.9	66.4	2.67
DRY_F286	-25.7	-24.7	58.1	65.9	2.62
DRY_G309	-32.3	-30.1	66.6	64.9	2.69
DRY_G308	-32.8	-31.4	61.3	63.8	2.58
DRY_G307	-33.0	-31.8	58.6	64.5	2.56

⁽¹⁾ Air velocity 30 seconds after the beginning of the test

**Table 8 - Aerodynamic Performance Test Data :
Reference Fluid**

TEST CODE	T _a °C	T _f °C	Rh %	t _o ⁽¹⁾ μm	t _{end} ⁽²⁾ μm	FE ⁽³⁾ %	WC ⁽⁴⁾ %	V ⁽⁵⁾ m/s	δ* mm
M114A236	-0.5	1.0	84.2	1800	152	91.5	7.31*	67.6	6.18
M114A237	-0.1	0.8	92.7	1800	135	92.5	7.71*	67.3	6.03
M114A235	-1.0	0.6	81.9	1800	135	92.5	6.91*	67.1	6.25
M114C243	-11.2	-9.5	77.1	1800	196	89.1	2.93*	66.9	8.29
M114C242	-10.9	-9.9	72.6	1800	203	88.7	2.53*	67.2	8.46
M114C241	-11.4	-10.2	70.9	1800	185	89.7	2.53*	66.8	8.59
M114E246	-20.4	-19.1	61.8	1800	389	78.4	1.06	66.2	11.21
M114E244	-21.5	-19.8	59.5	1800	424	76.4	0.80	65.8	11.72
M114E245	-20.6	-20.0	60.7	1800	406	77.4	0.66	66.1	11.52
M114F240	-25.5	-24.2	56.3	1800	610	66.1	0.66	65.0	12.87
M114F239	-25.8	-24.6	53.3	1800	643	64.3	0.53	64.6	13.33
M114F238	-26.0	-25.0	53.8	1800	627	65.2	0.40	65.2	13.12

*caution value outside the ± 2% range

-
- (1) Thickness of the fluid measured at the beginning of the test.
(2) Thickness of the fluid measured at the end of the test.
(3) Fluid Elimination.
(4) Water Change.
(5) Air velocity 30 seconds after the beginning of the test.

**Table 9 - Refractive Index Data and Water Change:
Reference Fluid**

TEST CODE	RI Initial	RI Final	Δ RI	WC % W/W	Rh %
M114A236	1.4277	1.4222	-0.0055	7.31*	84.2
M114A237	1.4277	1.4219	-0.0058	7.71*	92.7
M114A235	1.4277	1.4225	-0.0052	6.91*	81.9
M114C243	1.4277	1.4255	-0.0022	2.93*	77.1
M114C242	1.4276	1.4257	-0.0019	2.53*	72.6
M114C241	1.4277	1.4258	-0.0019	2.53*	70.9
M114E246	1.4277	1.4269	-0.0008	1.06	61.8
M114E244	1.4277	1.4271	-0.0006	0.80	59.5
M114E245	1.4275	1.4270	-0.0005	0.66	60.7
M114F240	1.4277	1.4272	-0.0005	0.66	56.3
M114F239	1.4276	1.4272	-0.0004	0.53	53.3
M114F238	1.4277	1.4274	-0.0003	0.40	53.8

*caution value outside the $\pm 2\%$ range

ARCTON LTD.
Arctica DG RTU, lot # 28

High Speed Ramp Test

AMIL 2013-06-27

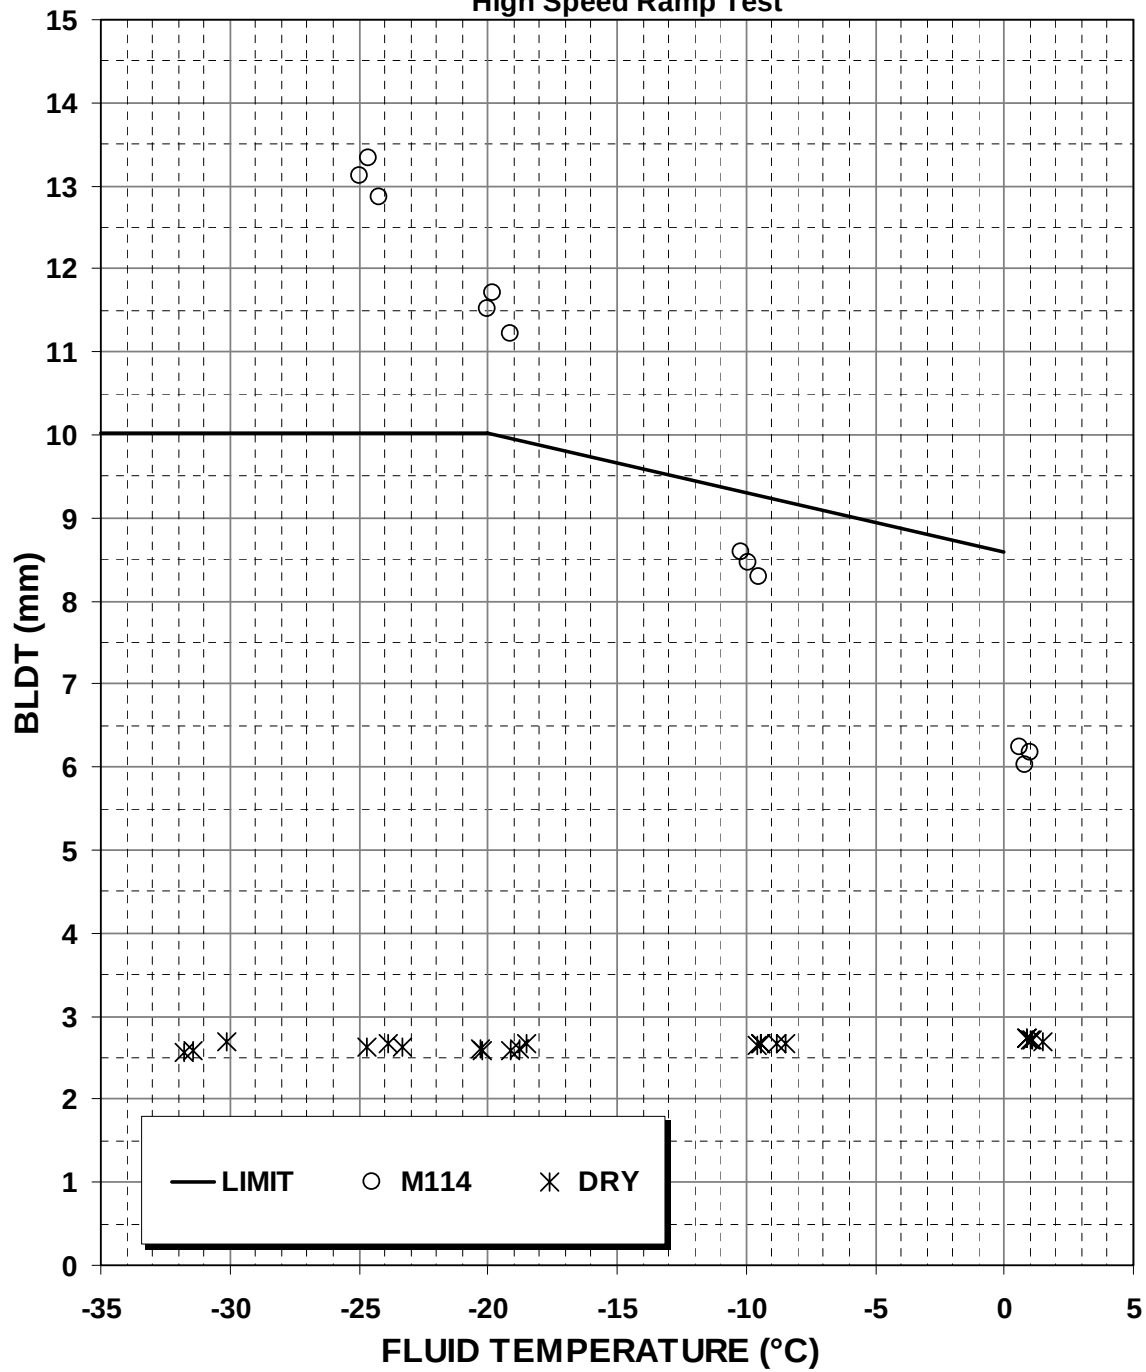


Figure 7 - Acceptance Criteria

3.3 Flat Plate Elimination Tests

BLDT, fluid elimination and water change values are listed in Table 4. In Figure 1, BLDT values are presented in comparison with the acceptance criteria. This figure shows that the candidate fluid **ARCTON LTD. Arctica DG RTU lot # 28** is acceptable with the high speed ramp above -30.5°C in the case of the Fluid as received.

4. REFERENCES

1. American Society for Testing and Materials "Standard Specification for Reagent Water", ASTM D 1193-06, 2011.
2. SAE International Aerospace Material Specification, "Deicing/Anti-icing Fluid, Aircraft, SAE Type I", AMS 1424, revision K, March 2012.
3. SAE International Aerospace Standard, "Standard Test Method for Aerodynamic Acceptance of SAE AMS 1424 and SAE AMS 1428 Aircraft Deicing/Anti-icing Fluids", AS5900, revision B, July 1, 2007.
4. Laforte, J.-L., P. Louchez, G. Bouchard, and M. Farzaneh, "A Facility to Evaluate Performance of Aircraft Ground De/Anti-Icing Fluids Subjected to Freezing Rain". *Cold Regions Science and Technology*, 1990. **18**: p. 161-171.
5. Laforte, J.-L., P. Louchez, and G. Bouchard, "Experimental Evaluation of Flat Plate Boundary Layer Growth over an Anti-Icing Fluid Film". *Canadian Aeronautics and Space Journal*, 1993. **39**(2): p. 96-104.

ATTACHMENT 1

Measurement Principle*

The time varying velocity at the inlet of the test section will be derived from the measurement of the pressure difference $P_1 - P_2$, recorded as a function of time during all test runs. For such purpose, the following relation, obtained from application of Bernoulli and continuity equations according to usual wind tunnel practice, will be used:

$$V = \sqrt{\frac{2(P_1 - P_2)}{\rho} \left/ \left(1 - \left[\frac{S_2}{S_1} \right]^2 \right) \right.} \quad (1)$$

where ρ is the mass per unit volume of the test gas at the test conditions, and S_1/S_2 is the area ratio of the wind tunnel contraction.

The boundary layer displacement thickness (BLDT) on the bottom flat plate, at the location of the pressure tap P_3 (cross-section 3), will be evaluated from the measurement of the two pressure differences $P_1 - P_2$ and $P_1 - P_3$ recorded as functions of time during all the test runs.

Indeed, an increase in BLDT from inlet to outlet of the test section causes a restriction of the net cross-sectional area, thus producing an increase in the air velocity along the test section, which in turn causes a decrease of static pressure from cross-section 2 to 3.

* This text reproduces Appendix B of DOCUMENT NO D6-55573: "Aerodynamic Acceptance Test for Aircraft Ground Deicing/Anti-icing Fluids". BOEING Commercial Airplane Company.

More precisely, the average BLDT δ_{ave}^* over the test section perimeter, at cross-section 3, will be evaluated using following relation, obtained from application of mass conservation and Bernoulli equations:

$$\delta_{ave}^* = \frac{1}{c} \left[S_3 - S_2 \sqrt{\frac{P_1 - P_2}{(P_1 - P_2) + (P_2 - P_3)}} \right] \quad (2)$$

where c is the test section perimeter at cross-section 3, and S_2 and S_3 are the areas of cross-sections 2 and 3 respectively.

When no fluid is present on the bottom flat plate, all four test section walls are in the same dry state, and the previous expression (2) yields the value of the BLDT on a dry wall:

$$\delta_{dry}^* = \delta_{ave}^* \quad (\text{with no fluid})$$

On the other hand, when the bottom plate of the test section is covered with a layer of de/anti-icing fluid, and the top and sides are not, the BLDT is not constant over the perimeter of the cross-section 3. Indeed, it assumes a value δ^* on the bottom plate and another value on the sides and top wall. Expressing the previously determined δ_{ave}^* as a perimeter-weighted average of δ_{dry}^* and δ^* , the following relation can be obtained:

$$\delta^* = \frac{c}{b} \left[\delta_{ave}^* - \frac{c-b}{c} \delta_{dry}^* \right] \quad (3)$$

where b is the width of the bottom flat plate. This relation will be used to derive the BLDT over a wet surface, δ^* , from the measurement of δ_{ave}^* carried out as explained with fluid on the bottom test section wall, provided an expression for

δ_{dry}^* has been previously determined by a number of "dry" runs, carried out without any fluid in the test section. More precisely, these dry runs, to be made during the setting up and calibration of the facility, will yield the value of δ_{dry}^* and they will be used to determine the constant in the following empirical formula:

$$\delta_{dry}^* = const \times \left[\frac{V}{n} \right]^{-1/5} \quad (4)$$

where V is the tunnel air velocity at cross-section 2 and n is the cinematic viscosity of the test gas at the test conditions. For data reduction of a test with fluid in the test section, this last expression (4) will be used to evaluate, as function of the instantaneous velocity determined by (1), the value of δ_{dry}^* to be used in expression (3).

This page left blank.

ATTACHMENT 2

TEST DATA SHEETS

DRY RUNS 37


RUNS WITH REFERENCE FLUID M114..... 59

Arctica DG RTU lot # 28, Fluid as received J-162 73

This page left blank.

DRY RUNS

DRY_A277

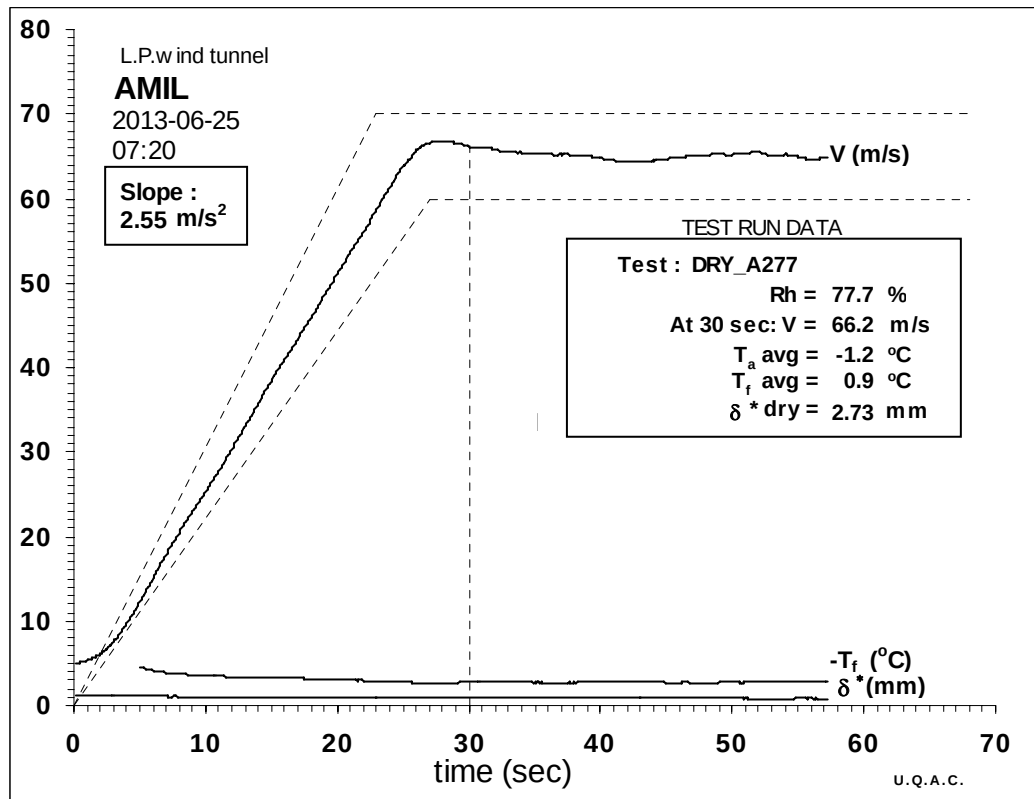

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-1.4	0.9	76.7	11.46	66.7	-0.20	2.60
28	-1.4	0.9	76.6	11.60	67.1	-0.11	2.75
29	-1.4	0.9	76.7	11.26	66.1	-0.15	2.68
30	-1.4	0.9	76.8	11.47	66.7	-0.12	2.74
31	-1.3	0.9	76.8	11.12	65.7	-0.12	2.73
32	-1.3	0.9	77.2	11.05	65.5	-0.11	2.74
33	-1.3	0.9	77.0	11.05	65.5	-0.07	2.81


Averages between 27 and 33 seconds:

30	-1.3	0.9	76.8	11.29	66.2	-0.12	2.73
----	------	------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_A278

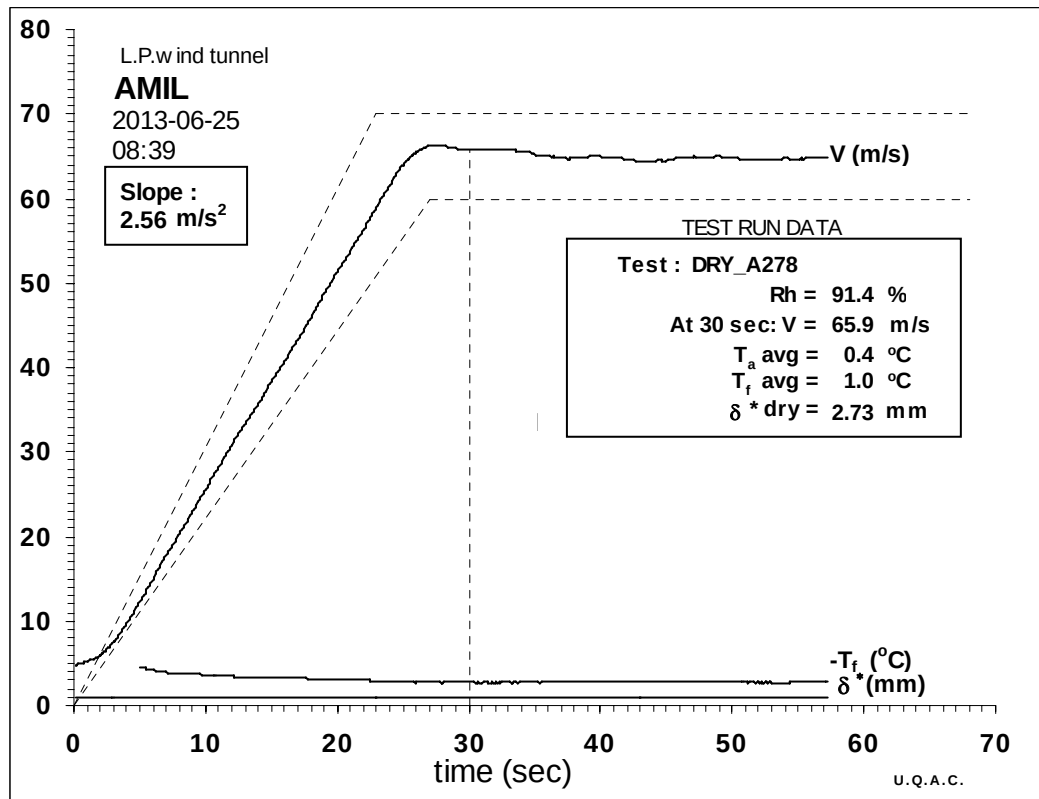

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ * mm
27	0.1	0.9	89.9	11.40	66.7	-0.17	2.65
28	0.1	1.0	90.2	11.15	66.0	-0.07	2.81
29	0.1	0.9	90.0	11.04	65.7	-0.12	2.73
30	0.1	0.9	90.1	11.04	65.7	-0.11	2.74
31	0.1	1.0	90.3	11.16	66.0	-0.12	2.72
32	0.2	0.9	90.3	11.13	65.9	-0.15	2.68
33	0.2	0.9	90.6	11.17	66.0	-0.12	2.73


Averages between 27 and 33 seconds:

30	0.1	0.9	90.2	11.14	65.9	-0.12	2.73
----	-----	------------	------	-------	------	-------	-------------

Test Duct Dimensions :

$$S2 = 30802.589 \text{ mm}^2 \quad S3 = 33220.101 \text{ mm}^2 \quad B3 = 301.981 \text{ mm} \quad C3 = 824.408 \text{ mm}$$

DRY_A279

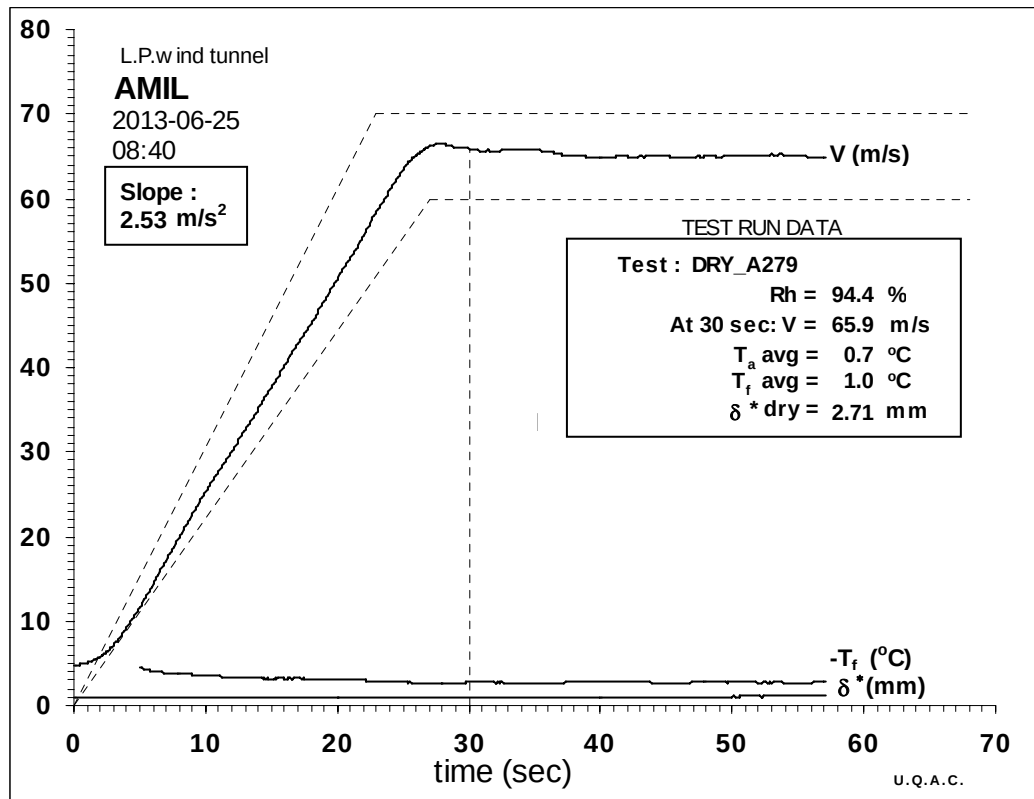

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ * mm
27	0.5	1.0	93.7	11.37	66.7	-0.24	2.53
28	0.6	1.0	93.9	11.22	66.2	-0.18	2.63
29	0.6	1.0	93.7	11.15	66.0	-0.13	2.72
30	0.6	1.0	93.9	11.02	65.6	-0.08	2.80
31	0.6	1.0	93.9	11.06	65.8	-0.11	2.75
32	0.6	1.0	94.2	10.95	65.4	-0.09	2.78
33	0.6	1.0	93.8	11.08	65.8	-0.18	2.63


Averages between 27 and 33 seconds:

30	0.6	1.0	93.9	11.10	65.9	-0.13	2.71
----	-----	------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_A280

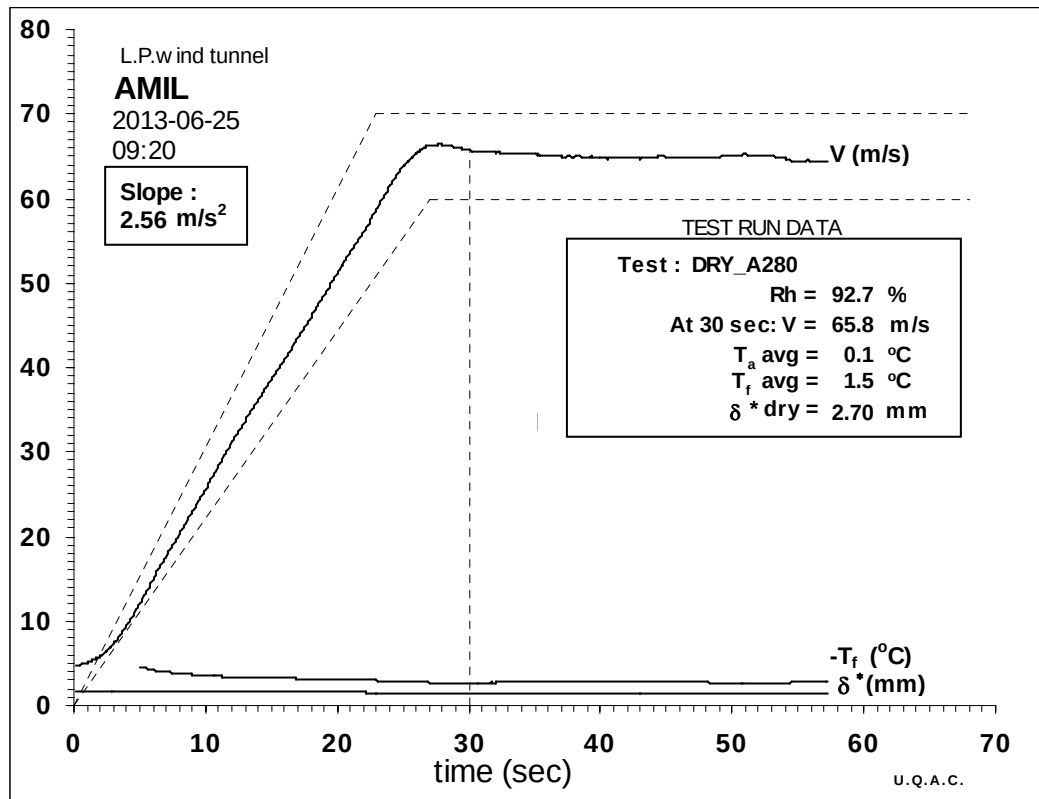

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.3	1.5	90.4	11.15	65.9	-0.14	2.70
28	-0.2	1.5	91.3	11.29	66.4	-0.17	2.64
29	-0.2	1.5	91.1	11.01	65.5	-0.12	2.73
30	-0.2	1.5	91.0	11.27	66.3	-0.18	2.62
31	-0.2	1.5	91.0	11.00	65.5	-0.14	2.70
32	-0.2	1.5	91.4	10.86	65.1	-0.10	2.76
33	-0.2	1.5	91.7	11.03	65.6	-0.11	2.75


Averages between 27 and 33 seconds:

30	-0.2	1.5	91.1	11.09	65.8	-0.14	2.70
----	------	------------	------	-------	------	-------	-------------

Test Duct Dimensions :

$$S2 = 30802.589 \text{ mm}^2 \quad S3 = 33220.101 \text{ mm}^2 \quad B3 = 301.981 \text{ mm} \quad C3 = 824.408 \text{ mm}$$

DRY_A282

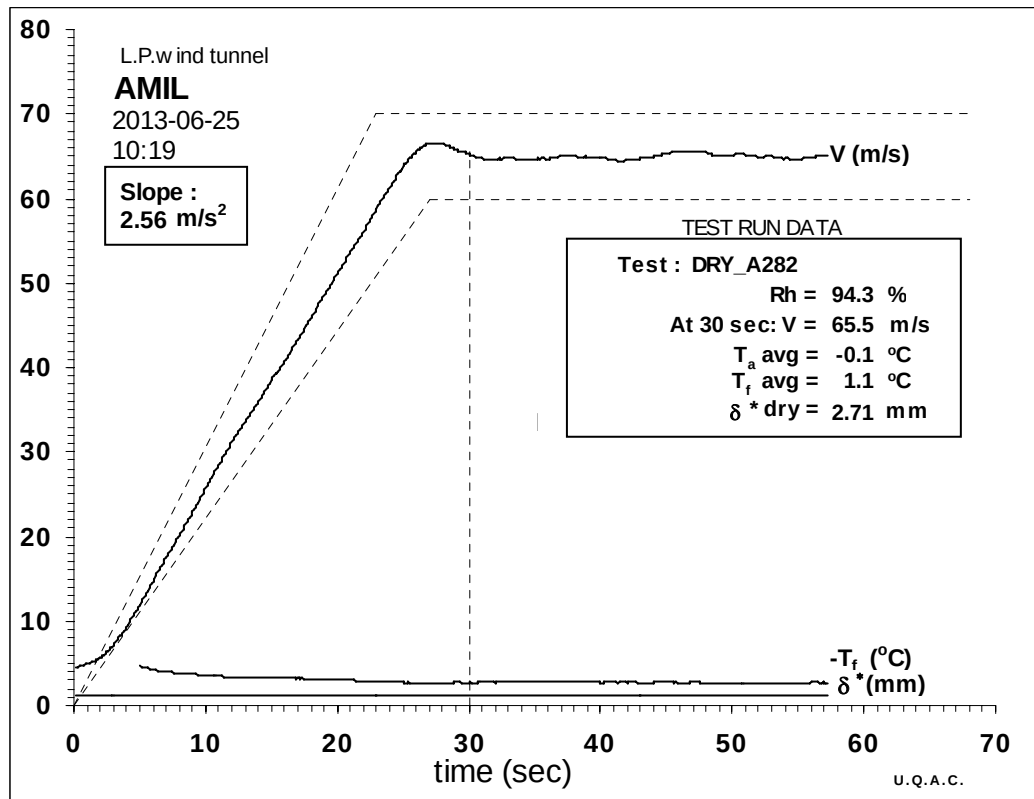

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.5	1.1	92.1	11.63	67.3	-0.14	2.70
28	-0.4	1.1	92.8	11.63	67.3	-0.15	2.69
29	-0.4	1.1	92.5	11.12	65.8	-0.13	2.71
30	-0.4	1.1	92.8	10.69	64.5	-0.10	2.75
31	-0.4	1.1	93.1	10.73	64.7	-0.14	2.68
32	-0.4	1.1	93.1	10.77	64.8	-0.14	2.68
33	-0.4	1.1	93.1	10.77	64.8	-0.08	2.79


Averages between 27 and 33 seconds:

30	-0.4	1.1	92.8	11.02	65.5	-0.13	2.71
----	------	------------	------	-------	------	-------	-------------

Test Duct Dimensions :

$$S2 = 30802.589 \text{ mm}^2 \quad S3 = 33220.101 \text{ mm}^2 \quad B3 = 301.981 \text{ mm} \quad C3 = 824.408 \text{ mm}$$

DRY_C289

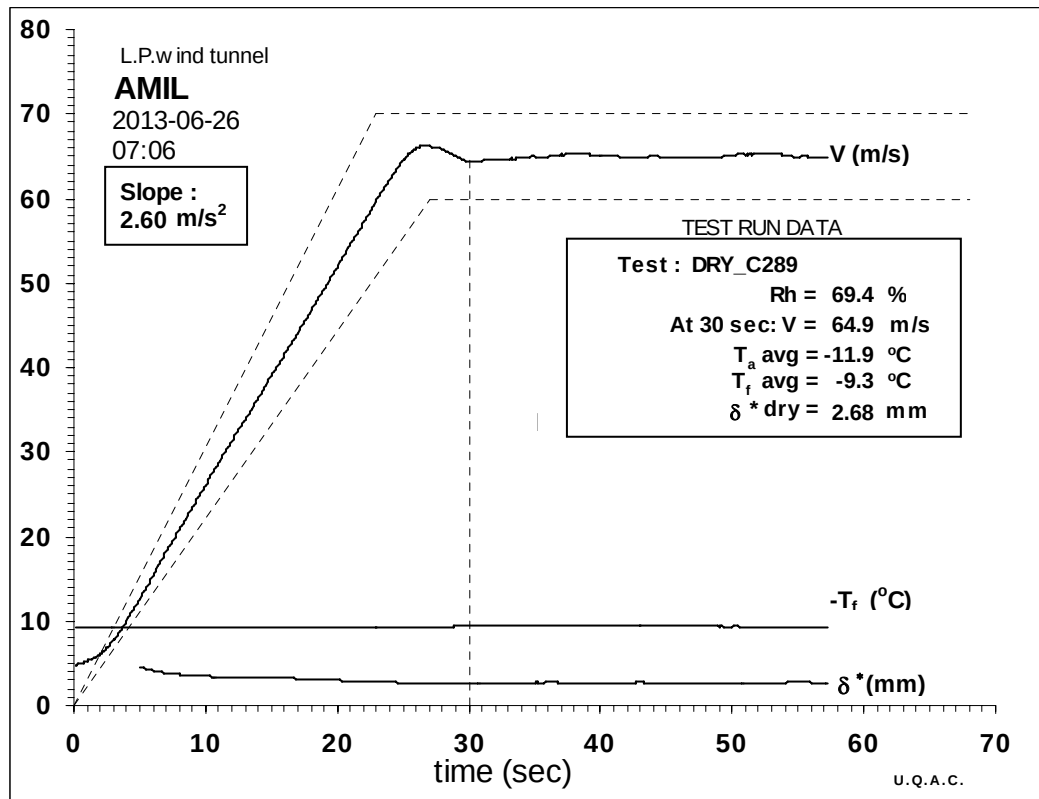

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-12.2	-9.4	68.3	12.20	67.5	-0.18	2.66
28	-12.1	-9.3	68.4	11.55	65.6	-0.11	2.75
29	-12.1	-9.3	68.8	11.02	64.1	-0.11	2.75
30	-12.0	-9.4	68.5	11.12	64.4	-0.21	2.58
31	-12.0	-9.3	68.6	11.13	64.4	-0.15	2.67
32	-12.0	-9.4	69.0	11.11	64.4	-0.13	2.72
33	-12.0	-9.4	68.9	11.40	65.2	-0.21	2.58


Averages between 27 and 33 seconds:

30	-12.1	-9.4	68.6	11.29	64.9	-0.15	2.68
----	-------	-------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_C290

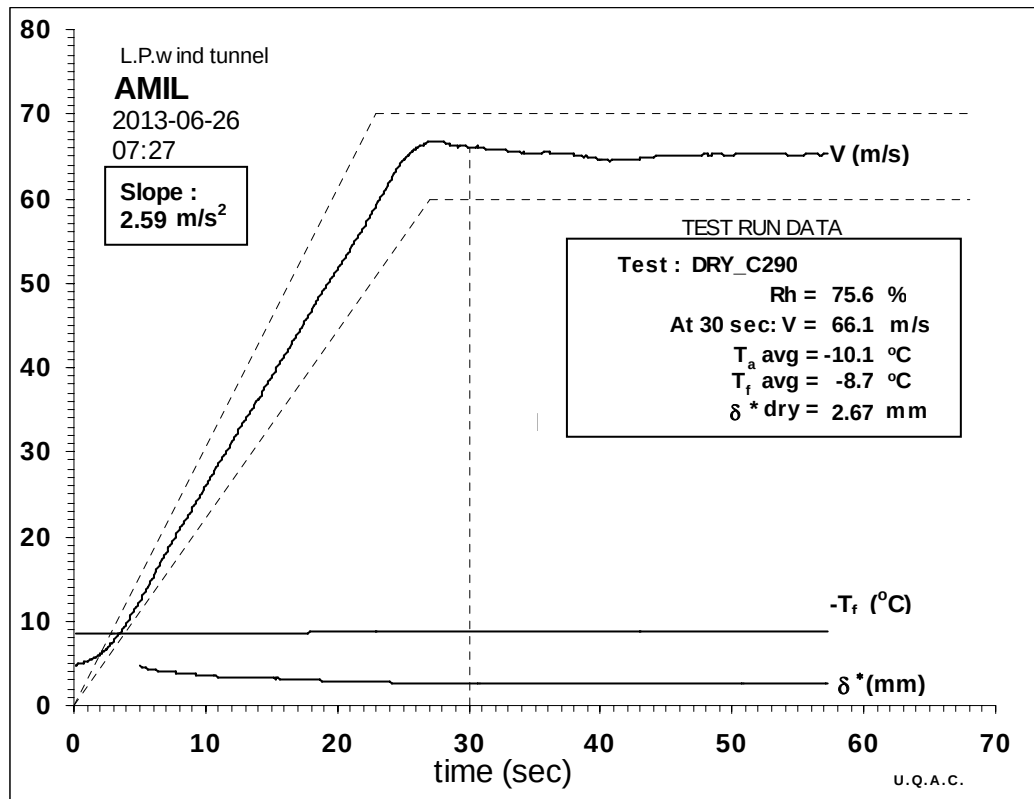

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-10.6	-8.7	74.4	11.83	66.6	-0.16	2.67
28	-10.6	-8.7	74.0	11.72	66.3	-0.20	2.61
29	-10.6	-8.7	73.8	11.58	65.9	-0.17	2.66
30	-10.5	-8.8	73.9	11.63	66.1	-0.17	2.66
31	-10.5	-8.8	73.9	11.72	66.3	-0.14	2.70
32	-10.5	-8.8	74.1	11.72	66.3	-0.17	2.66
33	-10.5	-8.8	74.0	11.30	65.1	-0.12	2.74


Averages between 27 and 33 seconds:

30	-10.5	-8.8	74.0	11.65	66.1	-0.16	2.67
----	-------	-------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_C291

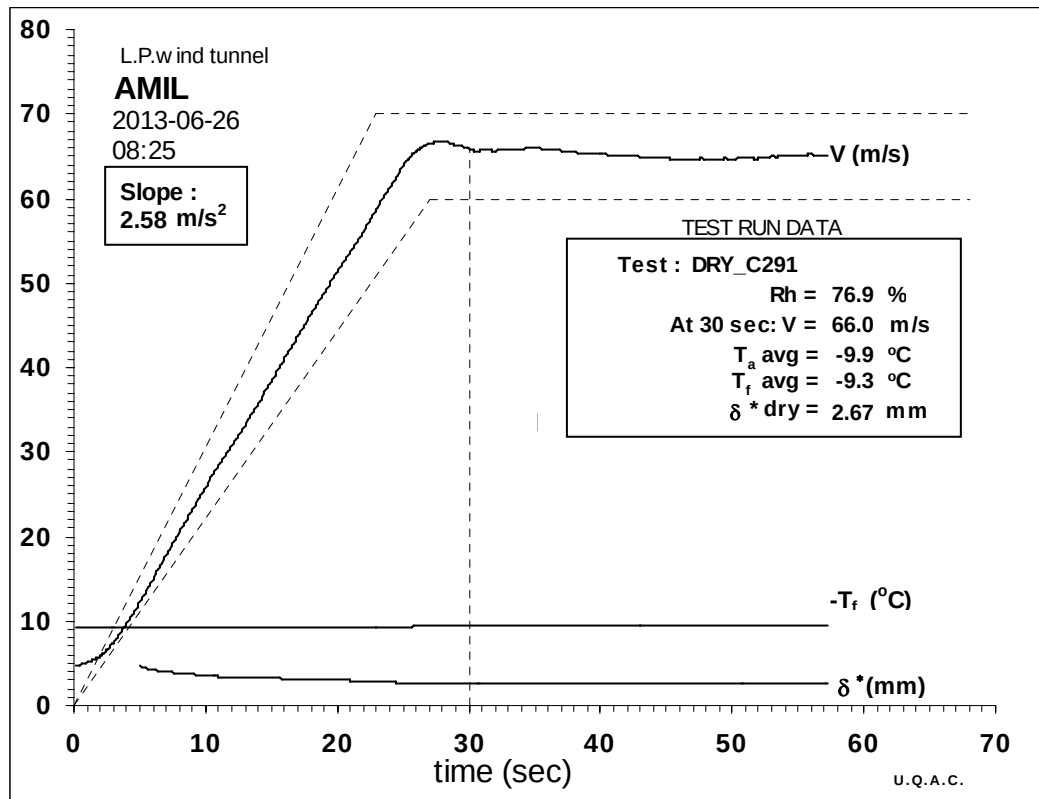

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ * mm
27	-10.4	-9.4	75.2	12.20	67.7	-0.16	2.69
28	-10.4	-9.4	75.3	11.95	67.0	-0.16	2.68
29	-10.4	-9.4	75.4	11.47	65.6	-0.18	2.63
30	-10.4	-9.4	75.1	11.59	66.0	-0.12	2.74
31	-10.3	-9.4	75.5	11.65	66.2	-0.15	2.69
32	-10.3	-9.4	75.3	11.17	64.8	-0.20	2.59
33	-10.3	-9.4	75.5	11.56	65.9	-0.12	2.74


Averages between 27 and 33 seconds:

30	-10.4	-9.4	75.3	11.62	66.0	-0.16	2.67
----	-------	-------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_C292

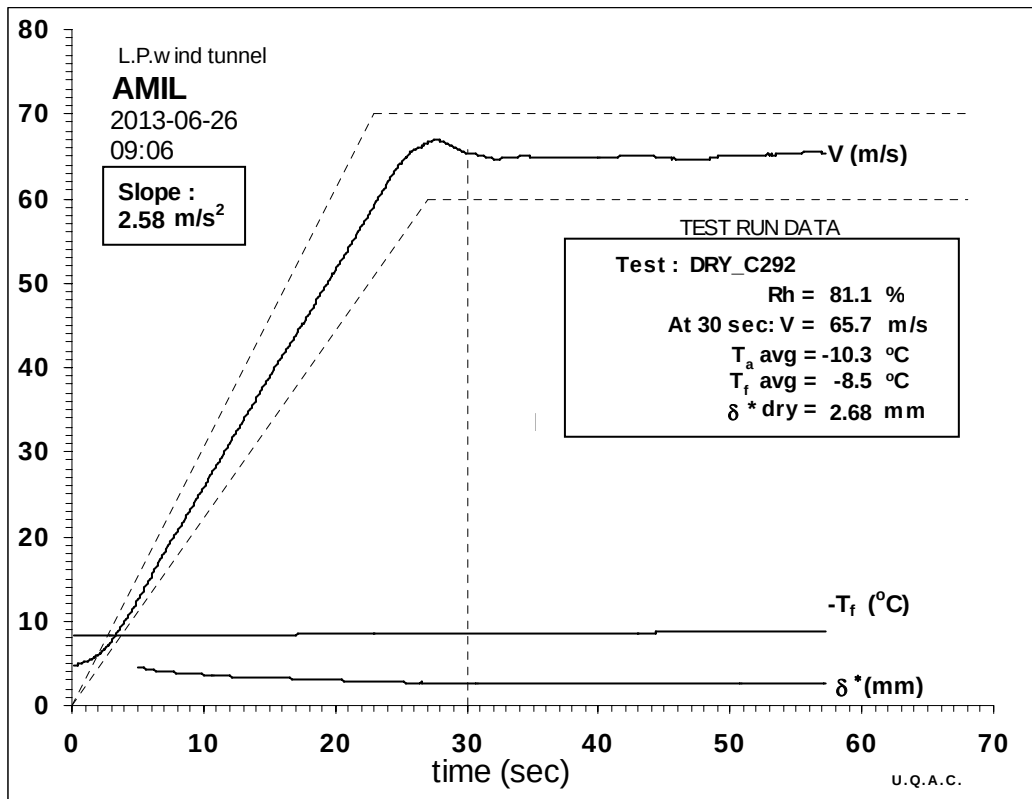

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-10.7	-8.5	79.0	12.07	67.3	-0.16	2.68
28	-10.7	-8.5	79.4	11.73	66.3	-0.13	2.72
29	-10.7	-8.5	79.6	12.08	67.3	-0.25	2.55
30	-10.7	-8.5	79.3	11.39	65.4	-0.14	2.69
31	-10.6	-8.6	79.7	11.00	64.2	-0.15	2.68
32	-10.6	-8.6	79.3	11.04	64.4	-0.13	2.71
33	-10.6	-8.6	79.7	11.41	65.4	-0.13	2.72


Averages between 27 and 33 seconds:

30	-10.7	-8.5	79.4	11.50	65.7	-0.16	2.68
----	-------	-------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_C294

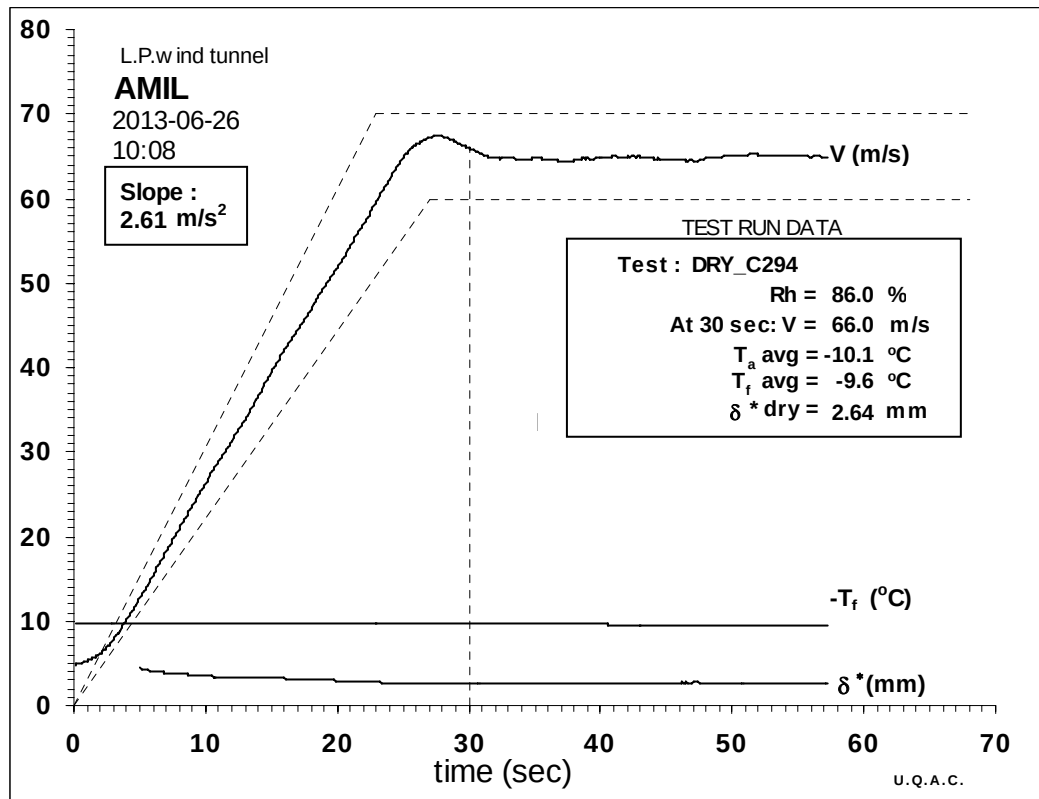

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-10.3	-9.6	85.1	12.68	69.0	-0.18	2.67
28	-10.4	-9.6	85.1	11.98	67.1	-0.18	2.65
29	-10.3	-9.6	85.3	12.13	67.5	-0.25	2.54
30	-10.3	-9.6	85.5	11.44	65.5	-0.20	2.60
31	-10.3	-9.6	85.5	11.32	65.2	-0.16	2.66
32	-10.3	-9.6	85.5	10.99	64.3	-0.14	2.69
33	-10.2	-9.6	85.9	11.08	64.5	-0.14	2.70


Averages between 27 and 33 seconds:

30	-10.3	-9.6	85.4	11.62	66.0	-0.18	2.64
----	-------	-------------	------	-------	------	-------	-------------

Test Duct Dimensions :

$$S2 = 30802.589 \text{ mm}^2 \quad S3 = 33220.101 \text{ mm}^2 \quad B3 = 301.981 \text{ mm} \quad C3 = 824.408 \text{ mm}$$

DRY_E295

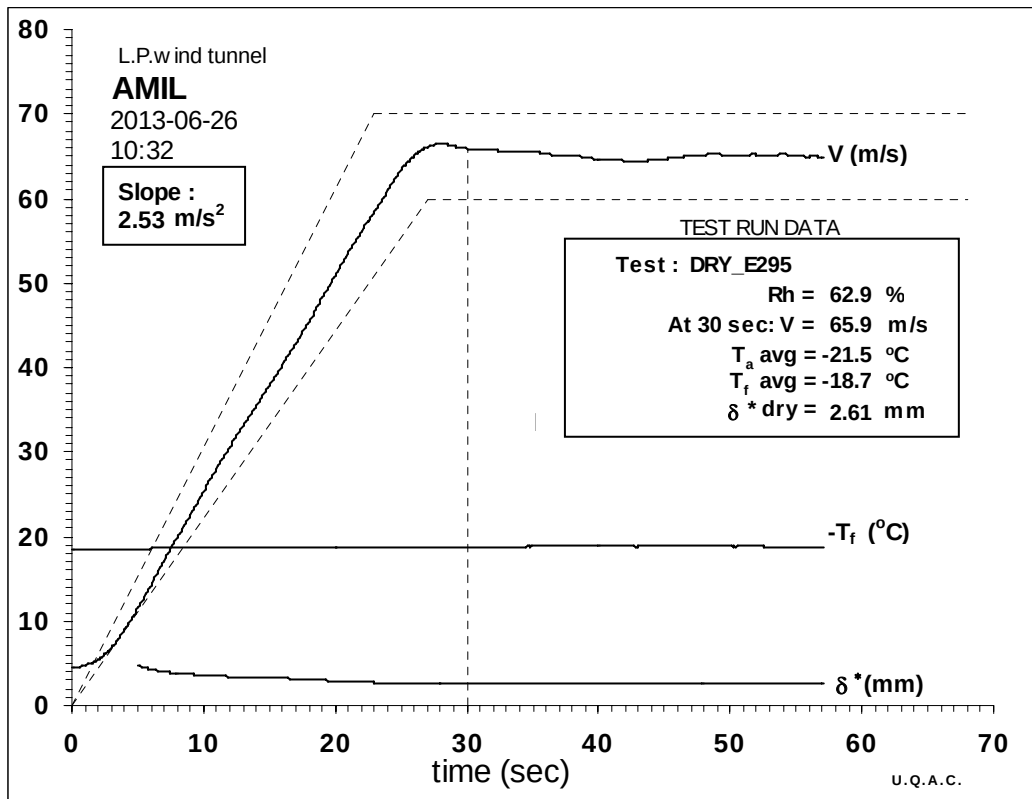

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-21.9	-18.8	61.8	12.37	66.6	-0.20	2.63
28	-21.9	-18.8	62.0	12.40	66.7	-0.21	2.61
29	-21.8	-18.8	62.0	11.91	65.4	-0.22	2.59
30	-21.8	-18.8	61.7	12.30	66.5	-0.19	2.64
31	-21.7	-18.8	61.8	12.04	65.8	-0.21	2.60
32	-21.7	-18.8	62.2	11.96	65.6	-0.20	2.62
33	-21.7	-18.8	61.7	11.80	65.1	-0.20	2.60


Averages between 27 and 33 seconds:

30	-21.8	-18.8	61.9	12.11	65.9	-0.20	2.61
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_E296

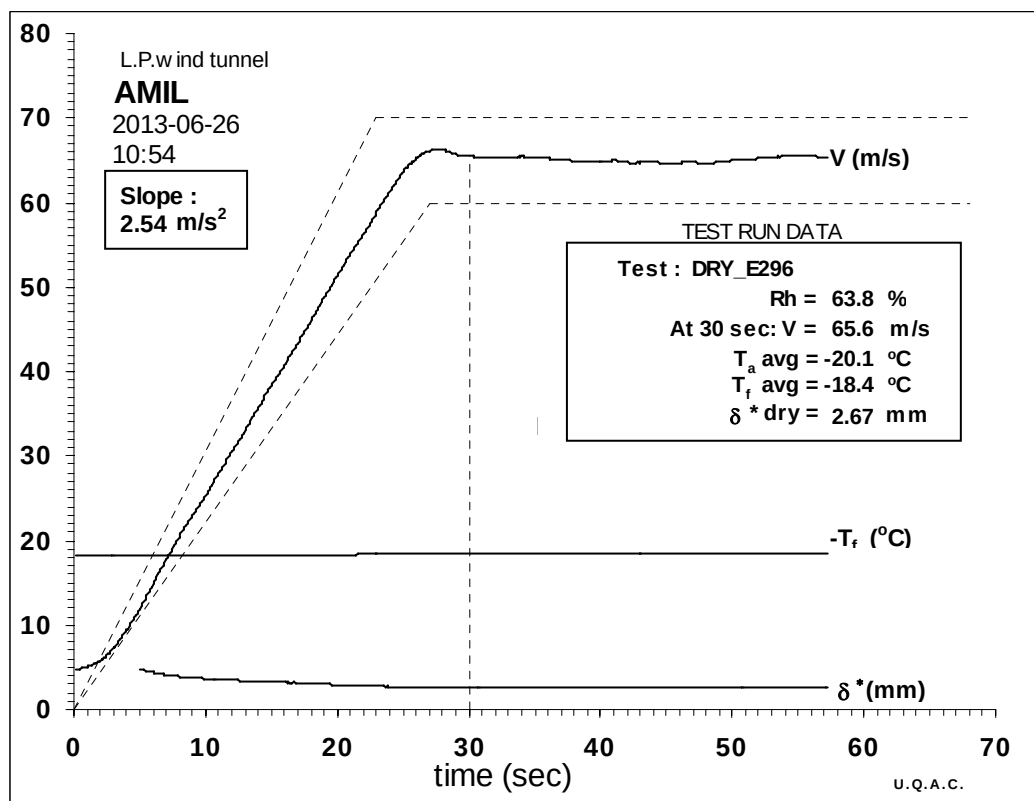

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-20.8	-18.4	62.6	12.14	66.2	-0.26	2.52
28	-20.8	-18.4	62.7	12.14	66.2	-0.21	2.61
29	-20.7	-18.4	62.3	11.98	65.7	-0.13	2.73
30	-20.7	-18.5	62.3	11.89	65.5	-0.15	2.69
31	-20.6	-18.5	61.9	11.60	64.7	-0.15	2.69
32	-20.6	-18.5	61.9	11.98	65.7	-0.15	2.69
33	-20.6	-18.5	62.1	11.72	65.0	-0.17	2.65


Averages between 27 and 33 seconds:

30	-20.7	-18.5	62.2	11.92	65.6	-0.17	2.67
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_E297

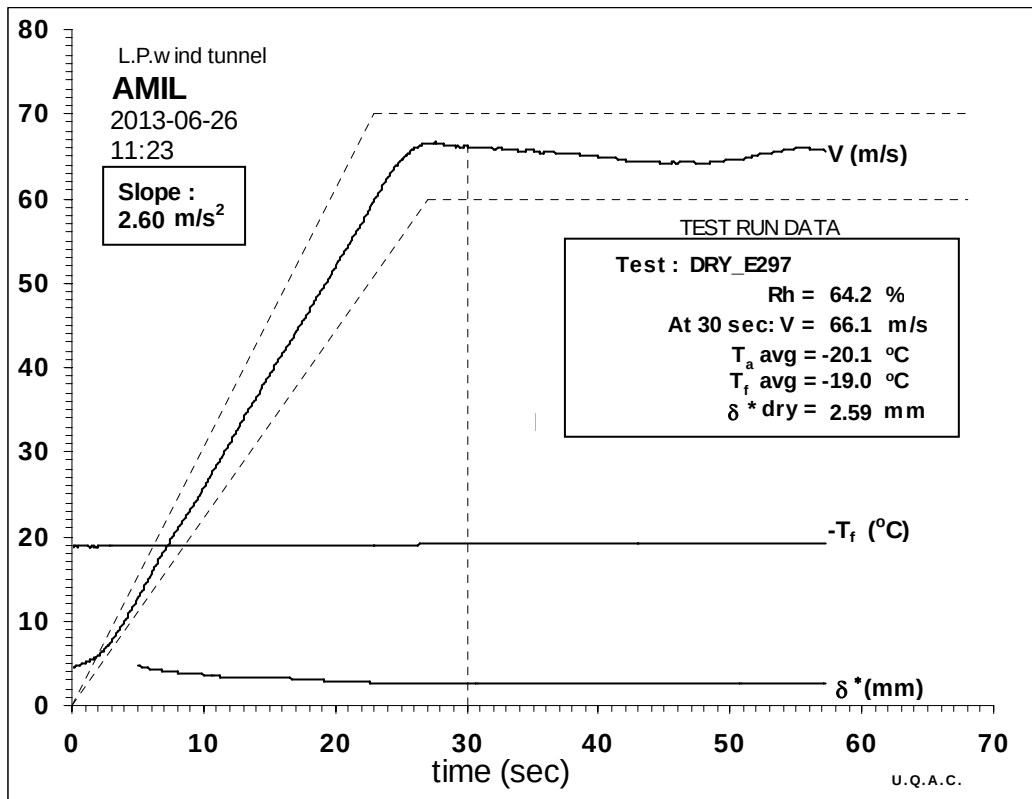

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ * mm
27	-20.8	-19.1	63.4	12.16	66.2	-0.30	2.46
28	-20.8	-19.1	63.1	12.16	66.2	-0.20	2.63
29	-20.8	-19.1	63.1	12.27	66.5	-0.22	2.60
30	-20.8	-19.1	62.7	12.02	65.8	-0.22	2.59
31	-20.7	-19.1	62.6	12.07	66.0	-0.14	2.71
32	-20.7	-19.1	62.4	11.97	65.7	-0.24	2.55
33	-20.6	-19.1	62.7	12.21	66.4	-0.25	2.54


Averages between 27 and 33 seconds:

30	-20.7	-19.1	62.8	12.12	66.1	-0.22	2.59
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_E298

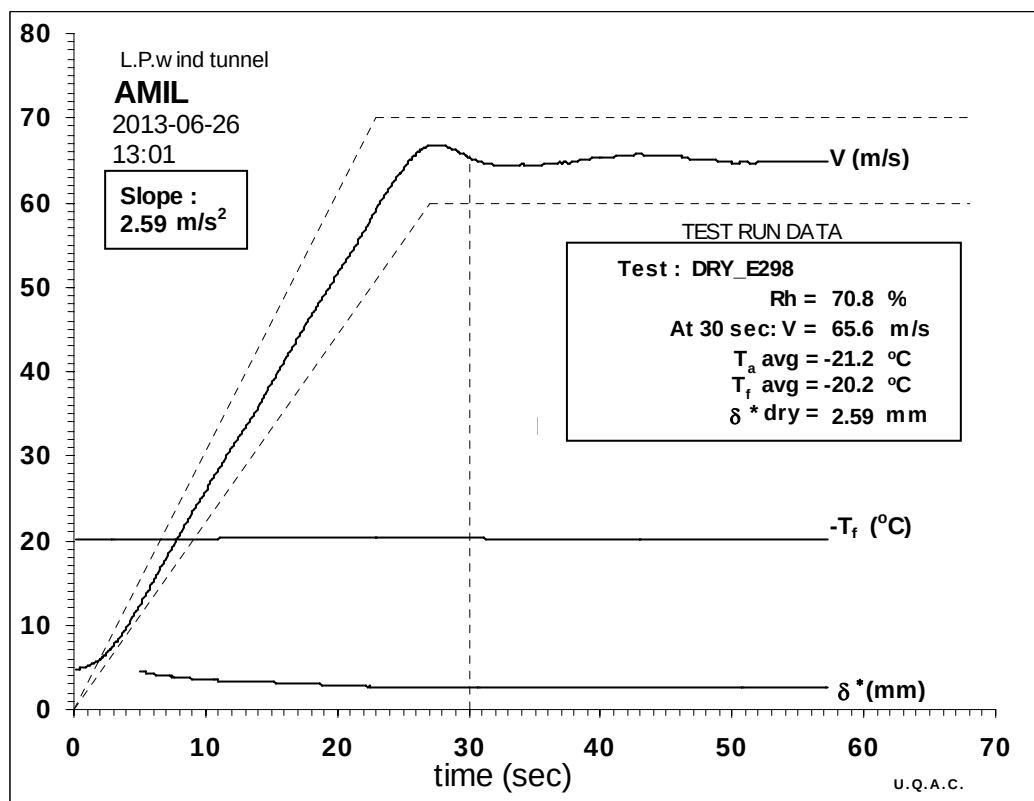

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-21.4	-20.3	70.3	12.77	67.8	-0.25	2.56
28	-21.4	-20.2	70.2	12.62	67.4	-0.26	2.54
29	-21.4	-20.2	70.0	12.20	66.2	-0.23	2.58
30	-21.3	-20.2	69.9	11.81	65.2	-0.21	2.60
31	-21.3	-20.2	70.2	11.50	64.3	-0.19	2.63
32	-21.2	-20.2	70.3	11.48	64.3	-0.22	2.58
33	-21.2	-20.2	70.3	11.65	64.8	-0.16	2.67


Averages between 27 and 33 seconds:

30	-21.3	-20.2	70.2	11.97	65.6	-0.22	2.59
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_E300

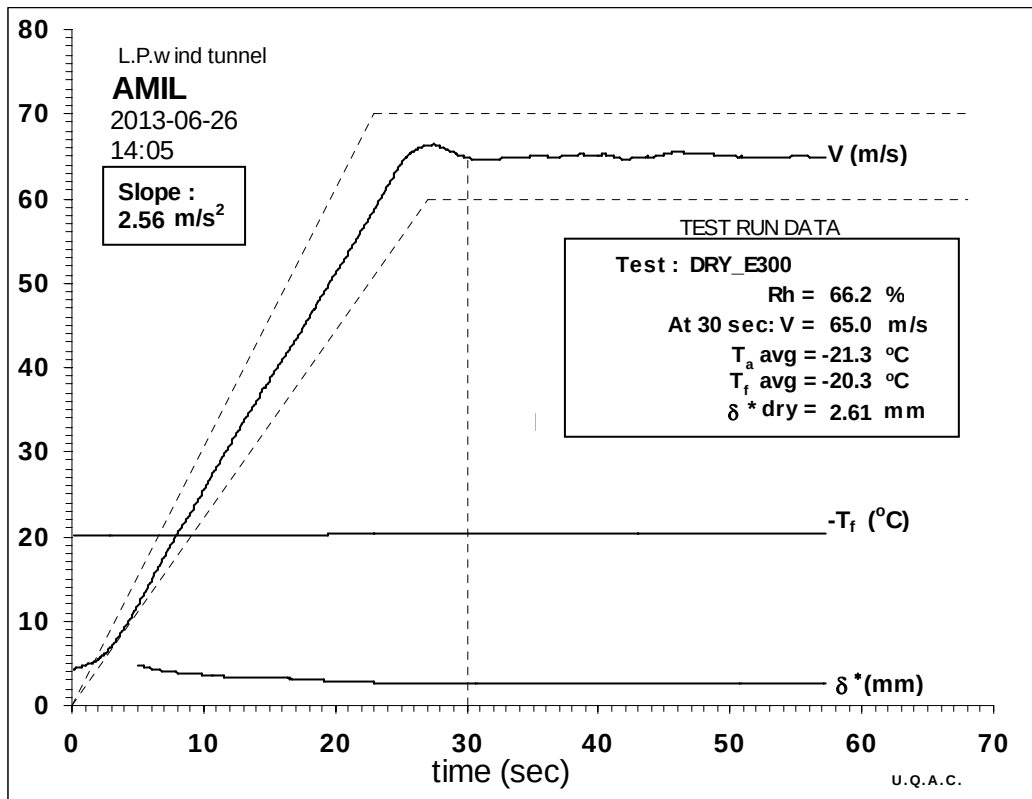

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-21.8	-20.3	65.3	12.70	67.5	-0.21	2.62
28	-21.8	-20.3	65.3	12.13	66.0	-0.20	2.61
29	-21.7	-20.3	65.3	11.76	65.0	-0.23	2.55
30	-21.7	-20.3	65.1	11.61	64.6	-0.21	2.58
31	-21.7	-20.4	65.0	11.66	64.7	-0.12	2.74
32	-21.6	-20.3	65.2	11.50	64.3	-0.25	2.52
33	-21.6	-20.4	65.2	11.39	64.0	-0.16	2.67


Averages between 27 and 33 seconds:

30	-21.7	-20.3	65.2	11.78	65.0	-0.20	2.61
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_F286

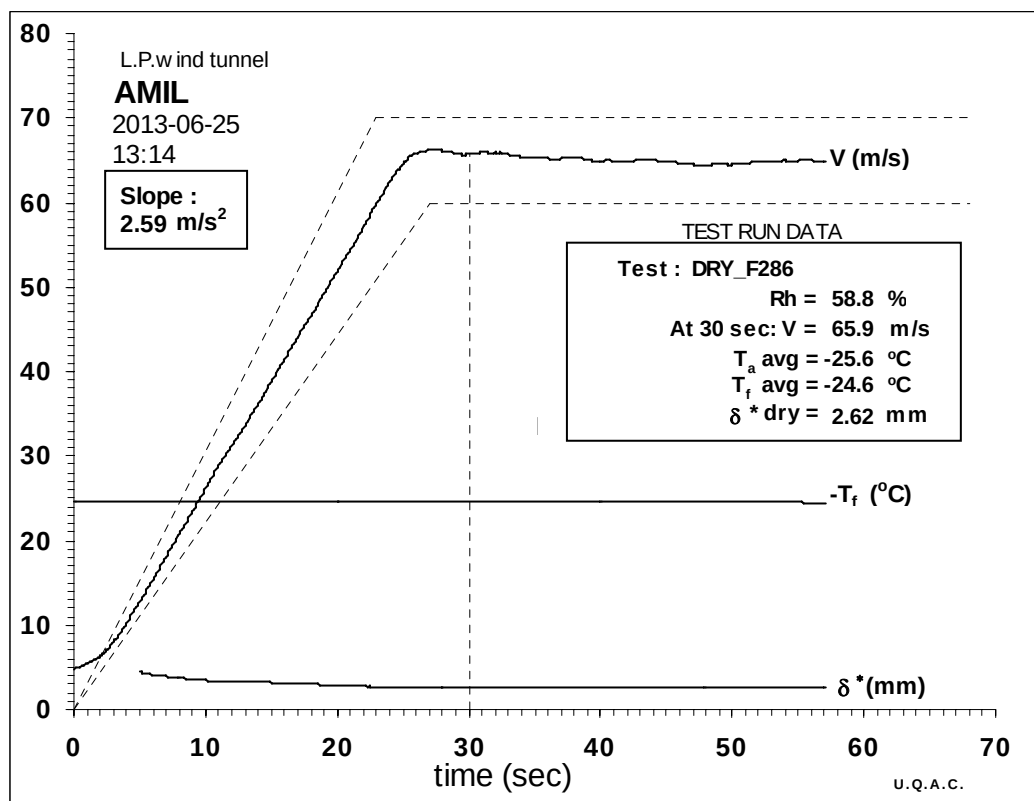

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-25.8	-24.7	57.7	12.78	67.2	-0.27	2.53
28	-25.8	-24.7	58.3	12.10	65.4	-0.26	2.52
29	-25.7	-24.7	57.8	12.15	65.5	-0.12	2.74
30	-25.7	-24.7	58.1	12.21	65.7	-0.15	2.70
31	-25.7	-24.7	58.1	12.32	66.0	-0.21	2.61
32	-25.6	-24.7	58.0	12.30	66.0	-0.17	2.67
33	-25.6	-24.7	58.4	12.42	66.3	-0.28	2.50


Averages between 27 and 33 seconds:

30	-25.7	-24.7	58.1	12.28	65.9	-0.20	2.62
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

$$S2 = 30802.589 \text{ mm}^2 \quad S3 = 33220.101 \text{ mm}^2 \quad B3 = 301.981 \text{ mm} \quad C3 = 824.408 \text{ mm}$$

DRY_F287

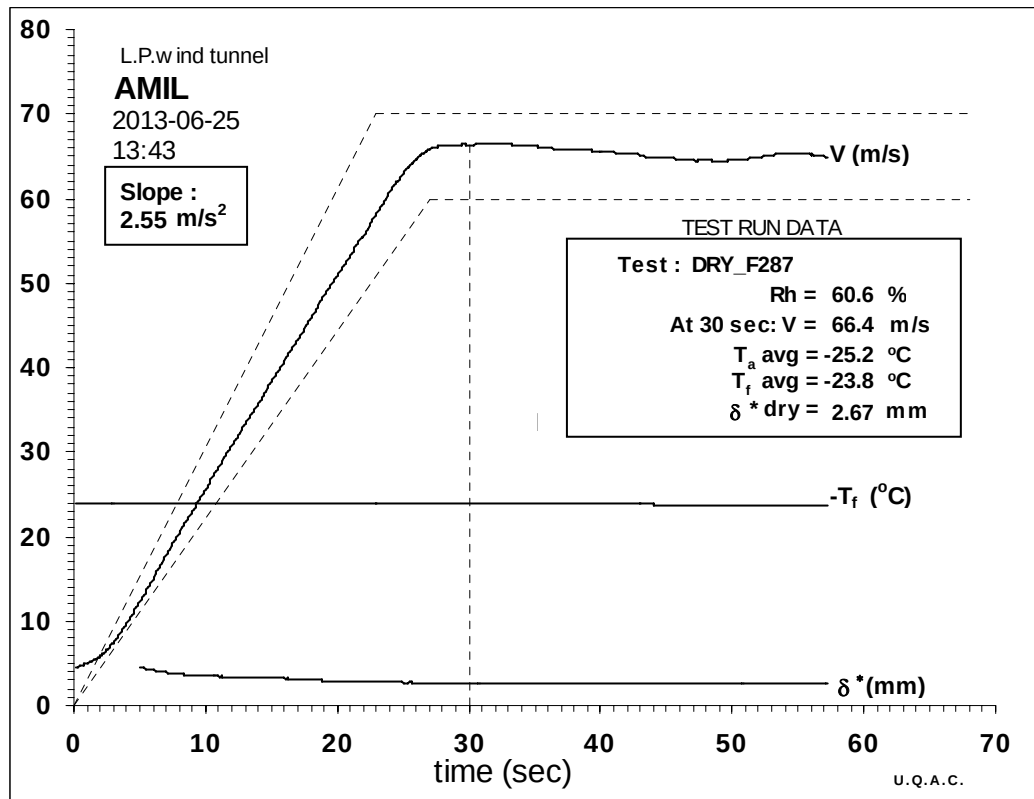

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-25.5	-23.9	59.9	12.38	66.2	-0.13	2.74
28	-25.5	-23.9	59.6	12.38	66.2	-0.20	2.63
29	-25.4	-23.9	60.0	12.44	66.4	-0.17	2.67
30	-25.4	-23.9	60.0	12.41	66.3	-0.18	2.66
31	-25.3	-23.9	59.9	12.57	66.7	-0.19	2.64
32	-25.3	-23.9	60.3	12.39	66.2	-0.15	2.71
33	-25.3	-23.9	59.8	12.56	66.7	-0.20	2.63


Averages between 27 and 33 seconds:

30	-25.4	-23.9	59.9	12.45	66.4	-0.18	2.67
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_F288

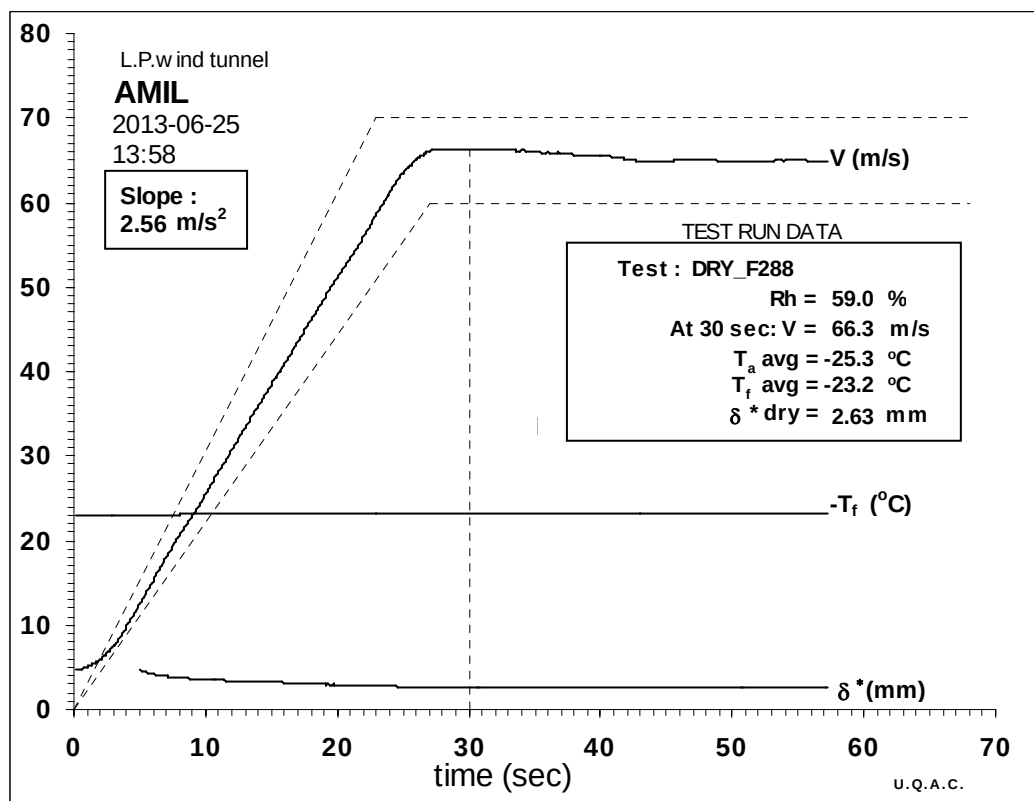

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-25.6	-23.2	58.4	12.32	66.0	-0.23	2.57
28	-25.6	-23.3	58.3	12.51	66.5	-0.22	2.60
29	-25.6	-23.3	58.2	12.47	66.4	-0.18	2.66
30	-25.5	-23.3	58.1	12.29	65.9	-0.19	2.64
31	-25.5	-23.3	57.8	12.45	66.4	-0.20	2.63
32	-25.4	-23.3	58.7	12.46	66.4	-0.17	2.67
33	-25.4	-23.3	58.6	12.42	66.3	-0.23	2.59


Averages between 27 and 33 seconds:

30	-25.5	-23.3	58.3	12.42	66.3	-0.20	2.63
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_G307

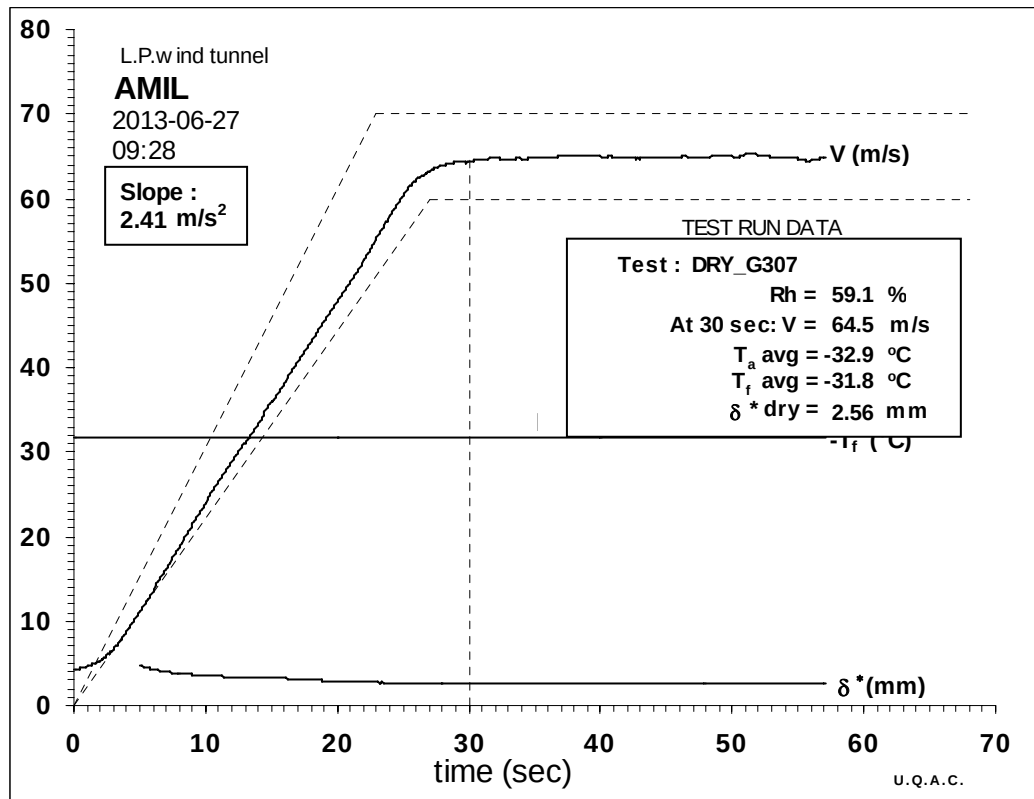

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-33.1	-31.8	58.6	12.21	64.7	-0.28	2.49
28	-33.1	-31.8	58.7	11.90	63.9	-0.23	2.57
29	-33.1	-31.8	58.6	11.90	63.9	-0.25	2.53
30	-33.0	-31.8	59.0	12.22	64.8	-0.24	2.56
31	-33.0	-31.8	58.5	12.17	64.6	-0.26	2.53
32	-33.0	-31.8	58.5	12.30	65.0	-0.20	2.63
33	-33.0	-31.8	58.5	12.13	64.5	-0.26	2.53


Averages between 27 and 33 seconds:

30	-33.0	-31.8	58.6	12.11	64.5	-0.24	2.56
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_G308

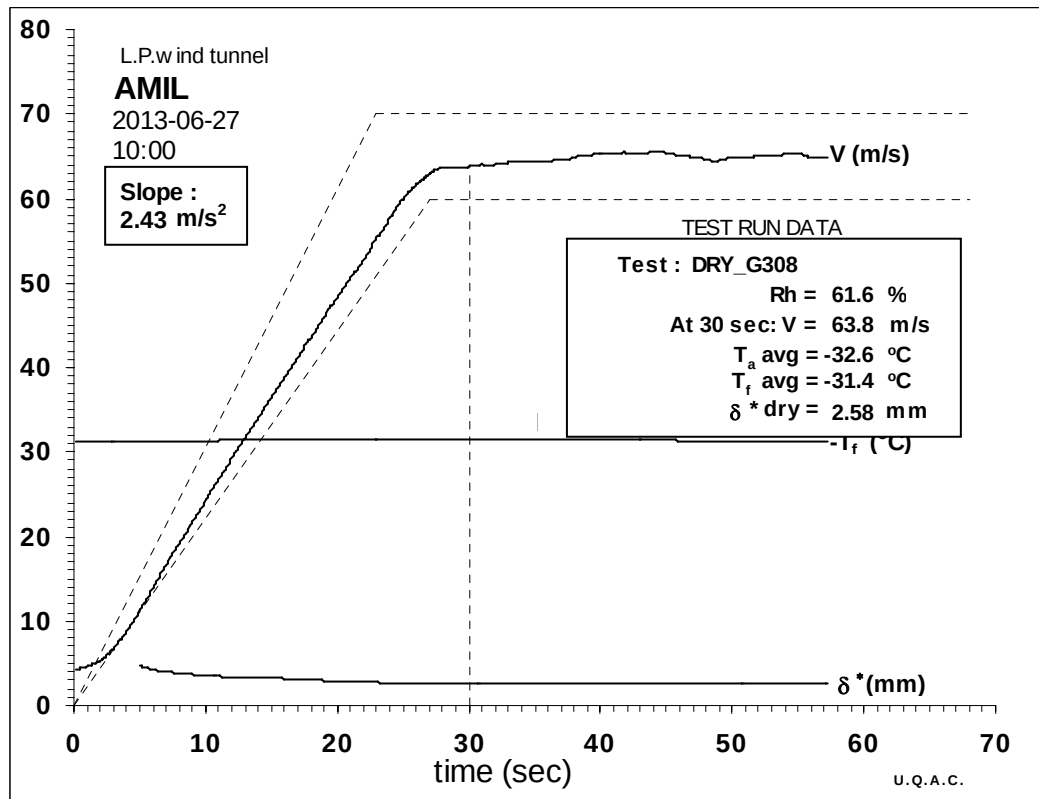

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-32.9	-31.4	61.1	11.63	63.2	-0.24	2.53
28	-32.9	-31.4	61.3	11.67	63.3	-0.19	2.63
29	-32.8	-31.4	61.4	12.03	64.3	-0.26	2.52
30	-32.8	-31.4	61.3	11.88	63.9	-0.18	2.65
31	-32.7	-31.4	61.0	11.61	63.1	-0.23	2.56
32	-32.7	-31.4	61.4	12.04	64.3	-0.20	2.62
33	-32.7	-31.4	61.2	12.09	64.5	-0.27	2.51


Averages between 27 and 33 seconds:

30	-32.8	-31.4	61.3	11.85	63.8	-0.22	2.58
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

DRY_G309

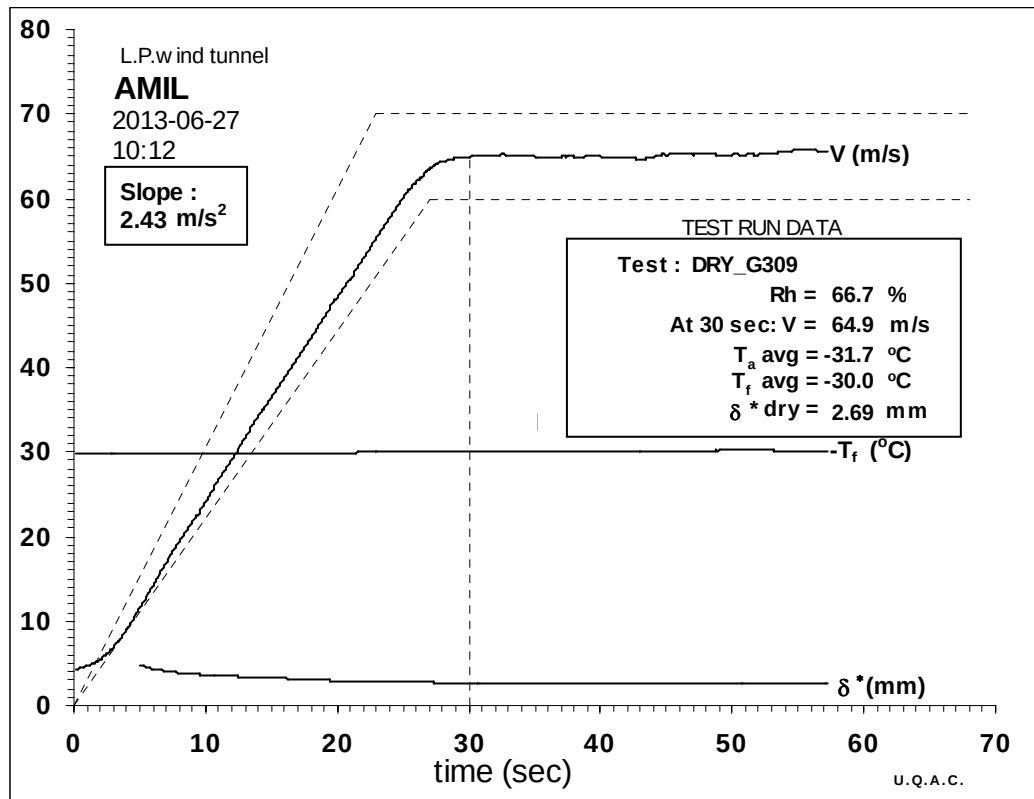

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-32.3	-30.0	66.9	11.92	64.1	-0.13	2.72
28	-32.3	-30.0	67.0	12.07	64.4	-0.07	2.82
29	-32.3	-30.1	66.3	12.47	65.5	-0.20	2.62
30	-32.3	-30.0	66.4	12.15	64.7	-0.16	2.68
31	-32.2	-30.1	66.6	12.24	64.9	-0.19	2.64
32	-32.3	-30.1	66.4	12.32	65.1	-0.13	2.73
33	-32.2	-30.1	66.3	12.50	65.6	-0.24	2.56

Averages between 27 and 33 seconds:


30	-32.3	-30.1	66.6	12.25	64.9	-0.16	2.69
----	-------	--------------	------	-------	------	-------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

RUNS WITH REFERENCE FLUID M114

M114A235

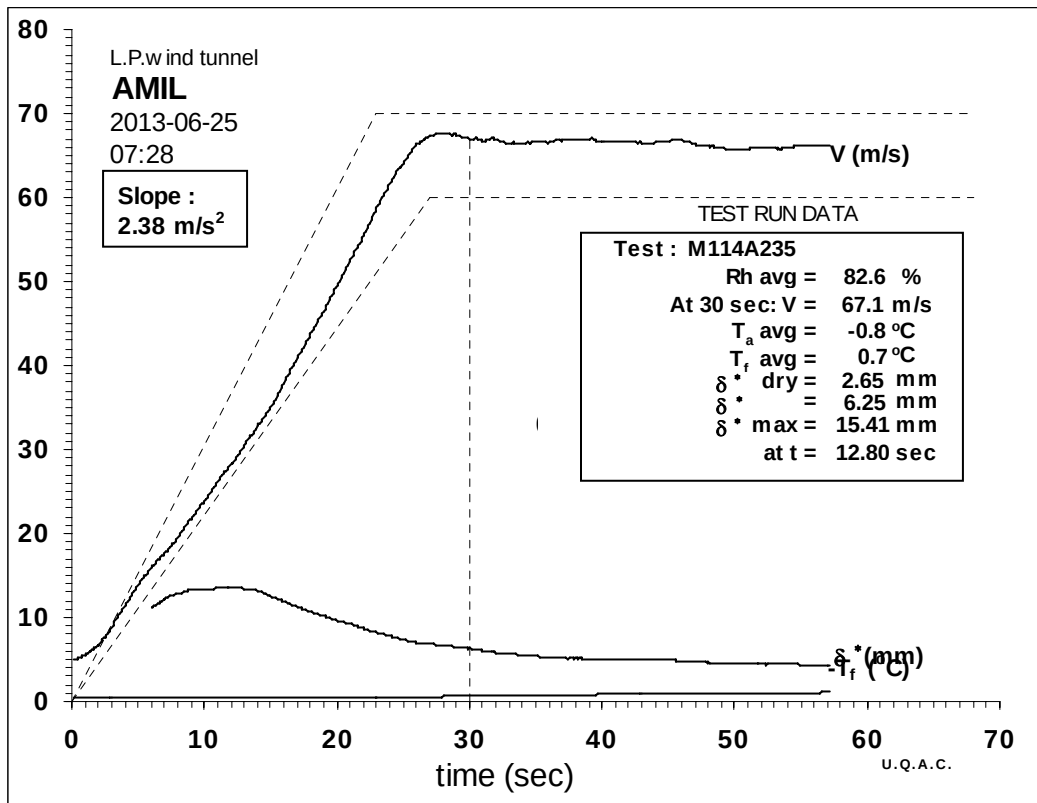

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-1.1	0.6	80.9	11.90	68.0	0.81	6.73
28	-1.1	0.6	81.6	11.68	67.4	0.74	6.50
29	-1.0	0.6	81.8	11.74	67.6	0.82	6.80
30	-1.0	0.6	81.9	11.51	66.9	0.67	6.26
31	-1.0	0.7	82.1	11.54	67.0	0.64	6.14
32	-0.9	0.7	82.2	11.46	66.8	0.53	5.67
33	-0.9	0.7	83.0	11.11	65.8	0.50	5.65


Averages between 27 and 33 seconds:

30	-1.0	0.6	81.9	11.57	67.1	0.67	6.25
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114A236

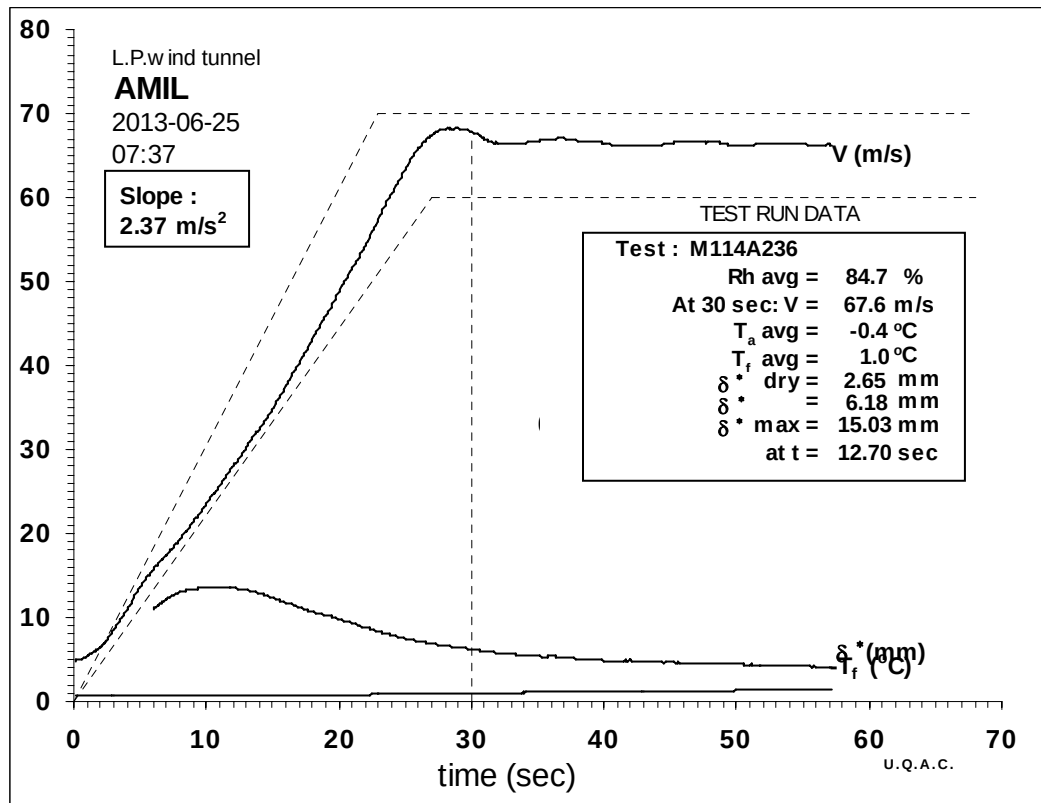

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.5	0.9	83.5	12.14	68.8	0.76	6.47
28	-0.5	0.9	83.7	12.01	68.4	0.80	6.64
29	-0.5	1.0	83.8	12.27	69.1	0.75	6.41
30	-0.5	1.0	83.7	11.71	67.5	0.72	6.39
31	-0.5	1.0	84.5	11.54	67.1	0.57	5.86
32	-0.4	1.0	84.8	11.40	66.7	0.56	5.85
33	-0.4	1.1	85.3	10.83	65.0	0.47	5.56


Averages between 27 and 33 seconds:

30	-0.5	1.0	84.2	11.72	67.6	0.67	6.18
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114A237

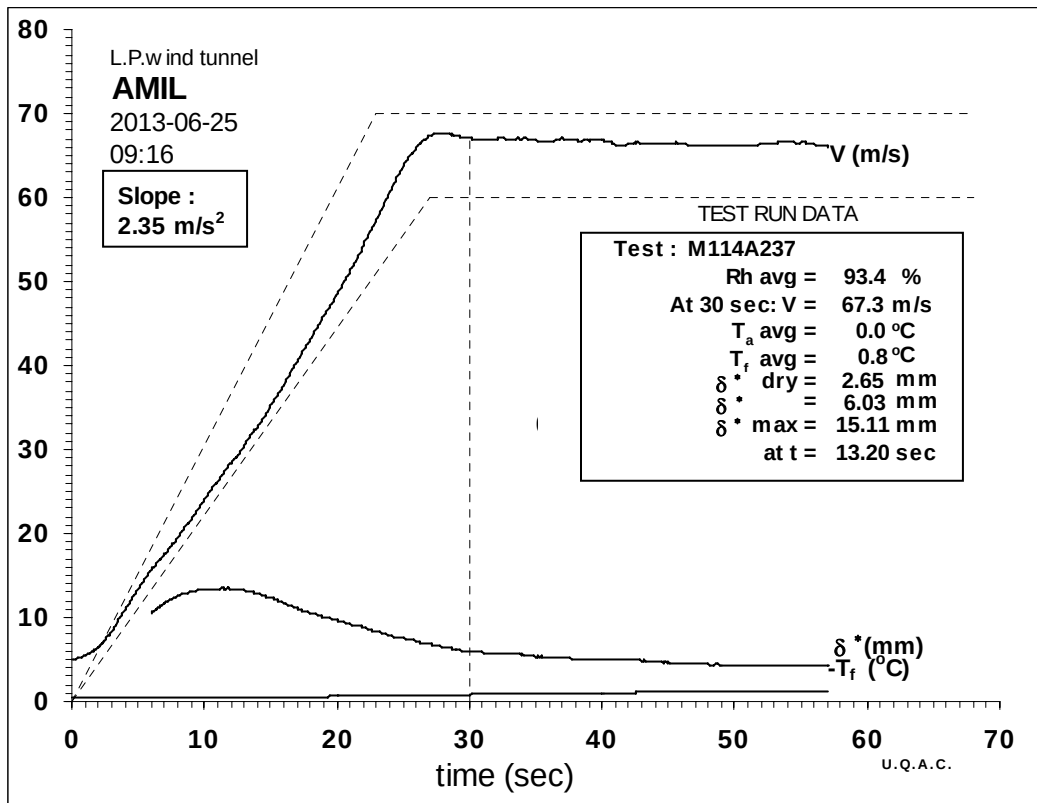

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.2	0.8	91.9	12.11	68.7	0.79	6.58
28	-0.2	0.8	92.3	11.80	67.8	0.71	6.35
29	-0.1	0.8	92.7	11.52	67.0	0.65	6.19
30	-0.1	0.8	92.4	11.31	66.4	0.59	5.96
31	-0.1	0.8	93.1	11.65	67.4	0.52	5.59
32	-0.1	0.9	93.1	11.53	67.1	0.53	5.69
33	-0.1	0.9	93.5	11.68	67.5	0.67	6.22


Averages between 27 and 33 seconds:

30	-0.1	0.8	92.7	11.62	67.3	0.62	6.03
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114C241

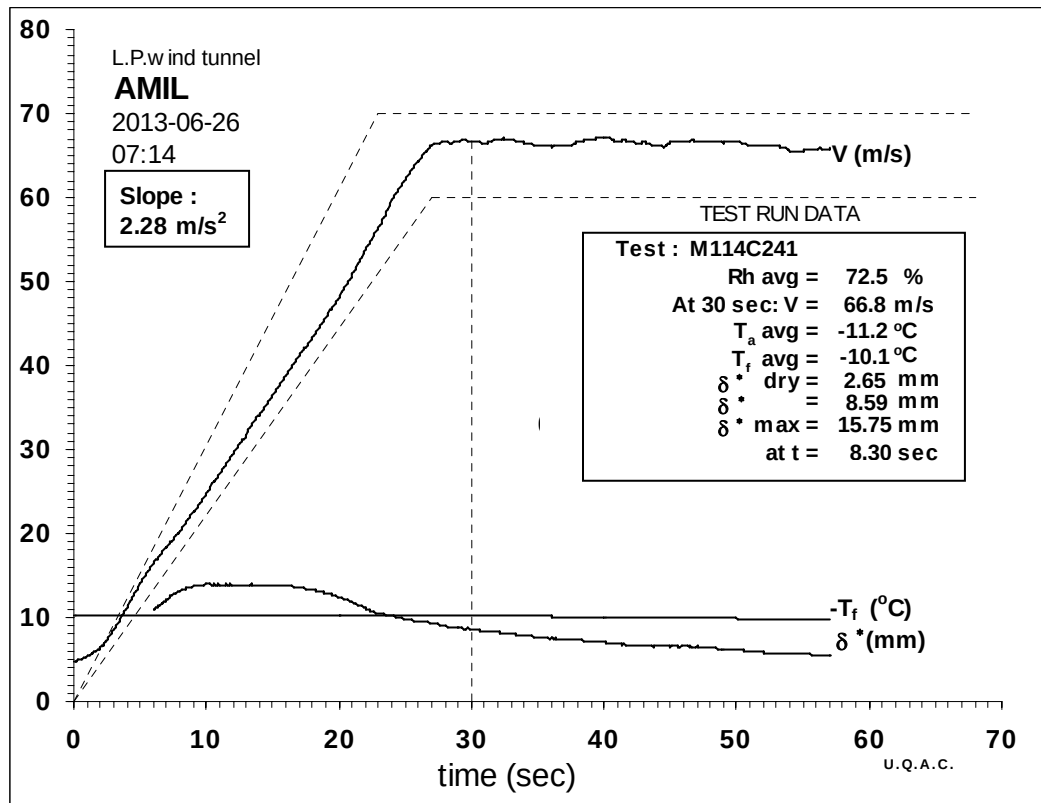

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-11.5	-10.2	70.2	11.88	66.6	1.43	9.07
28	-11.5	-10.2	70.6	12.27	67.7	1.46	8.97
29	-11.5	-10.2	70.5	11.93	66.8	1.34	8.71
30	-11.4	-10.2	71.0	11.48	65.5	1.25	8.56
31	-11.3	-10.2	71.1	12.07	67.2	1.29	8.46
32	-11.3	-10.2	71.2	11.88	66.7	1.22	8.29
33	-11.2	-10.2	71.9	11.90	66.7	1.18	8.13


Averages between 27 and 33 seconds:

30	-11.4	-10.2	70.9	11.92	66.8	1.31	8.59
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114C242

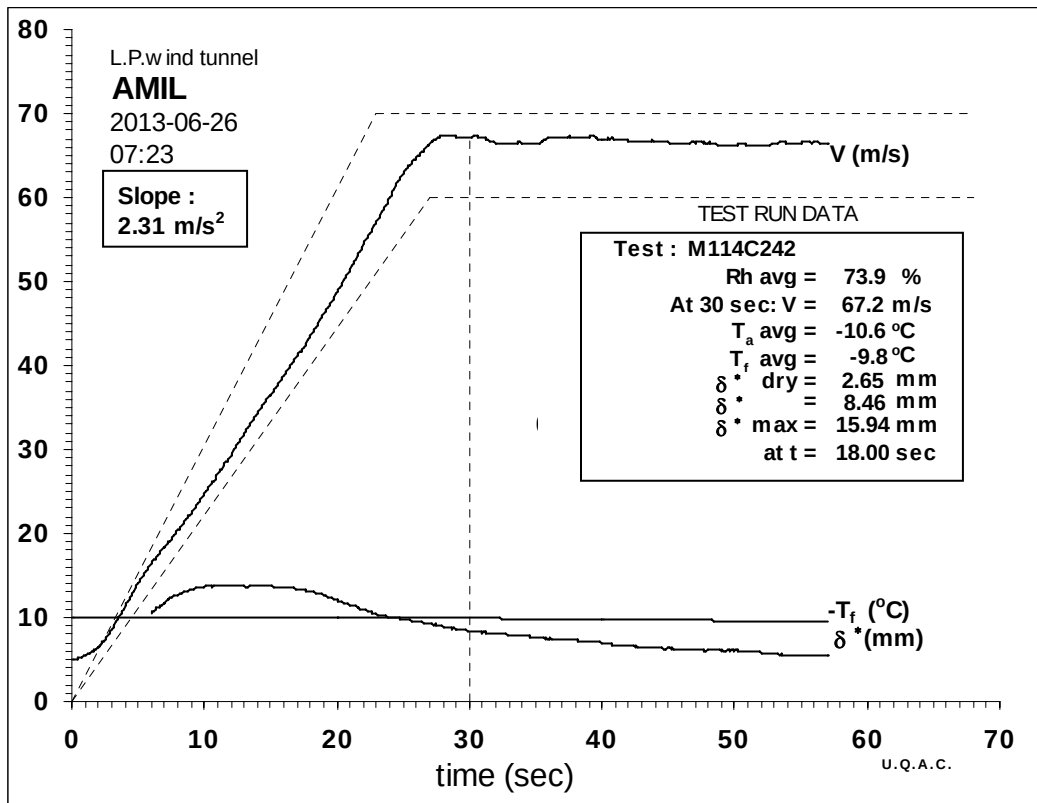

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-11.0	-9.9	71.6	11.88	66.7	1.45	9.14
28	-11.0	-9.9	72.1	11.95	66.9	1.46	9.11
29	-10.9	-9.9	72.5	12.28	67.8	1.34	8.54
30	-10.9	-9.9	72.6	12.16	67.5	1.23	8.23
31	-10.8	-9.9	73.0	11.74	66.3	1.22	8.32
32	-10.8	-9.9	72.8	12.17	67.5	1.20	8.10
33	-10.8	-9.9	73.1	11.98	67.0	1.13	7.89


Averages between 27 and 33 seconds:

30	-10.9	-9.9	72.6	12.04	67.2	1.29	8.46
----	-------	-------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114C243

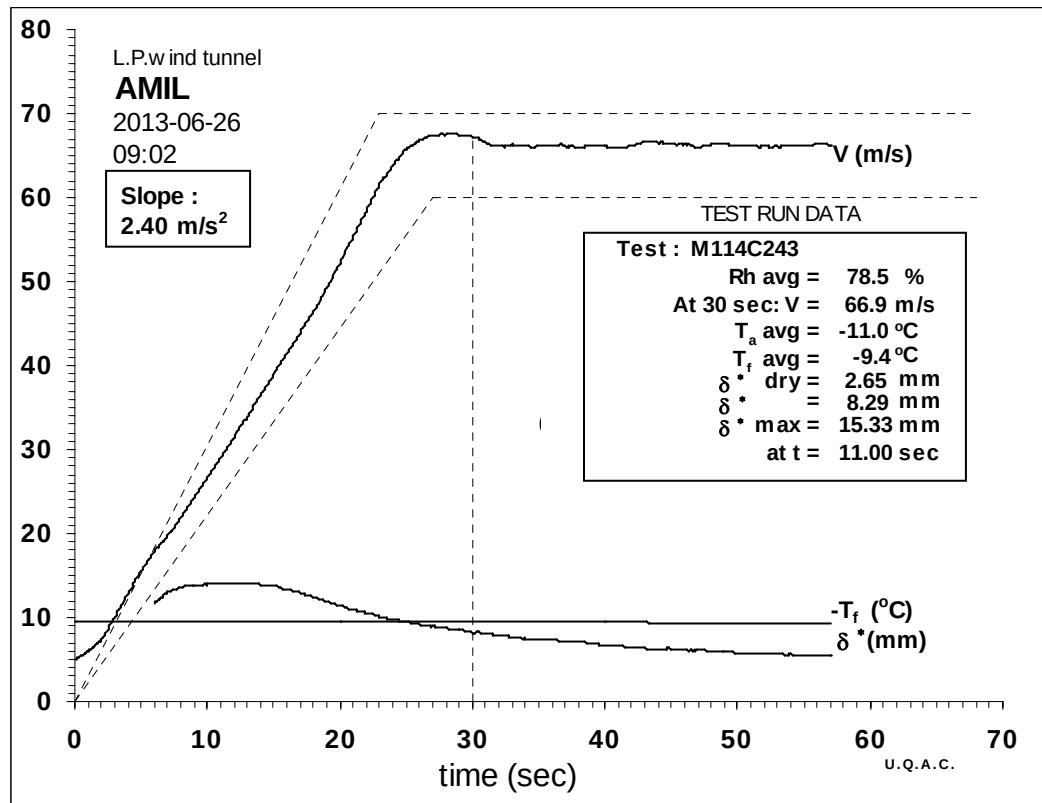

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-11.4	-9.5	76.4	11.97	66.9	1.42	8.97
28	-11.4	-9.5	76.7	12.12	67.3	1.31	8.52
29	-11.3	-9.5	77.1	12.38	68.0	1.36	8.59
30	-11.2	-9.5	77.0	12.24	67.7	1.31	8.48
31	-11.2	-9.5	77.3	11.89	66.7	1.18	8.11
32	-11.1	-9.5	77.2	11.53	65.7	1.05	7.76
33	-11.1	-9.5	78.0	11.36	65.2	1.01	7.70


Averages between 27 and 33 seconds:

30	-11.2	-9.5	77.1	11.96	66.9	1.23	8.29
----	-------	-------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114E244

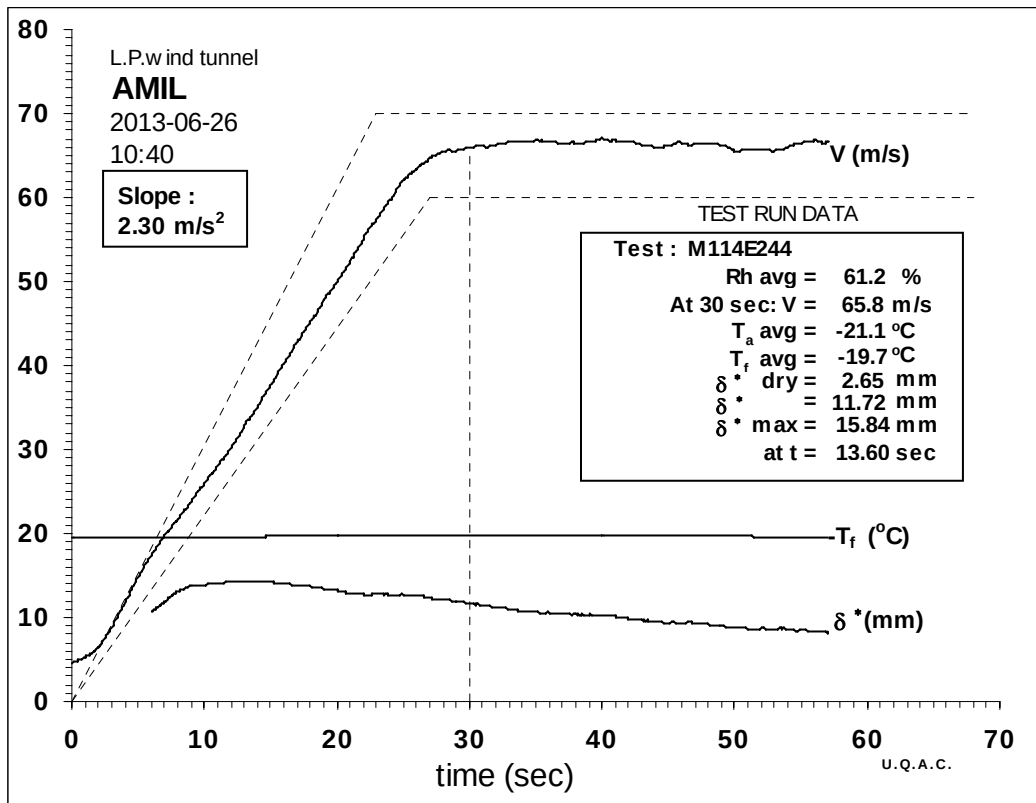

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-21.7	-19.8	59.3	11.73	64.9	2.33	12.24
28	-21.6	-19.8	59.7	11.72	64.9	2.37	12.38
29	-21.5	-19.8	59.2	12.04	65.8	2.26	11.82
30	-21.5	-19.8	59.5	12.28	66.4	2.24	11.60
31	-21.4	-19.8	59.5	12.01	65.7	2.21	11.68
32	-21.3	-19.8	59.8	12.30	66.5	2.08	11.08
33	-21.2	-19.8	59.5	11.91	65.5	2.11	11.40


Averages between 27 and 33 seconds:

30	-21.5	-19.8	59.5	12.03	65.8	2.23	11.72
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114E245

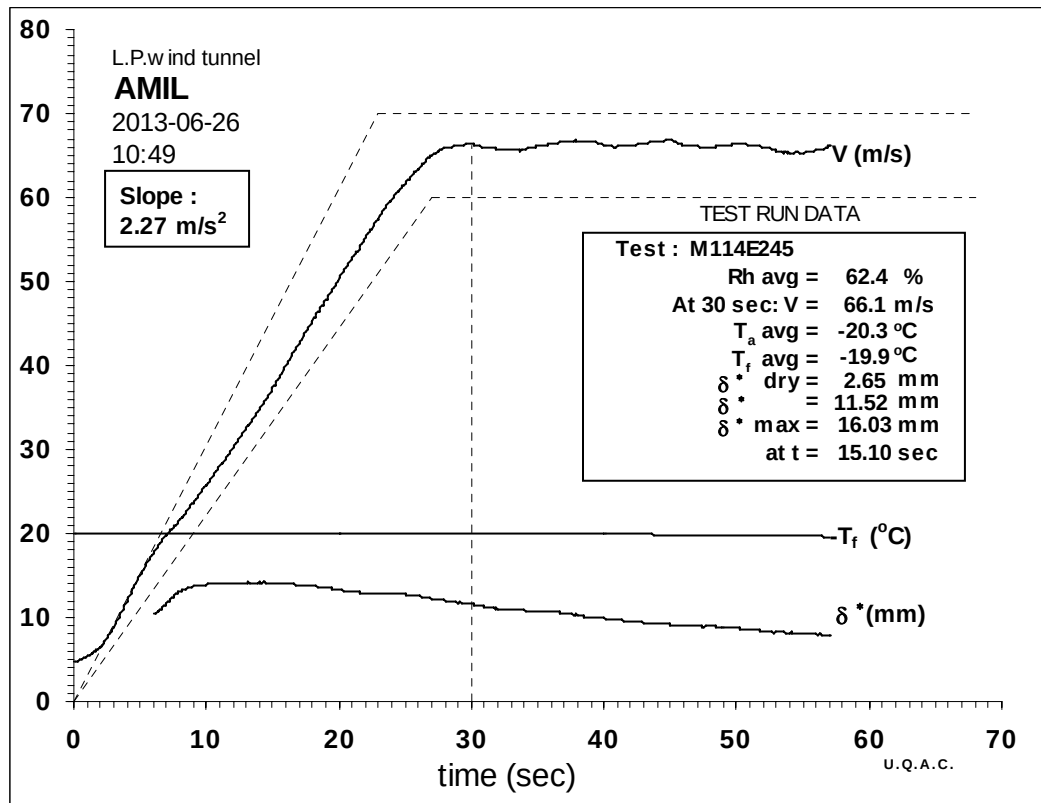

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-20.9	-20.0	60.9	11.83	65.3	2.23	11.86
28	-20.8	-20.0	60.6	12.19	66.3	2.37	12.09
29	-20.7	-20.0	60.3	12.35	66.7	2.35	11.93
30	-20.7	-20.0	60.4	12.31	66.6	2.19	11.44
31	-20.6	-20.0	60.9	11.91	65.5	2.15	11.54
32	-20.5	-20.0	61.0	11.93	65.6	2.00	11.00
33	-20.4	-20.0	61.2	12.08	66.1	1.89	10.55


Averages between 27 and 33 seconds:

30	-20.6	-20.0	60.7	12.10	66.1	2.18	11.52
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114E246

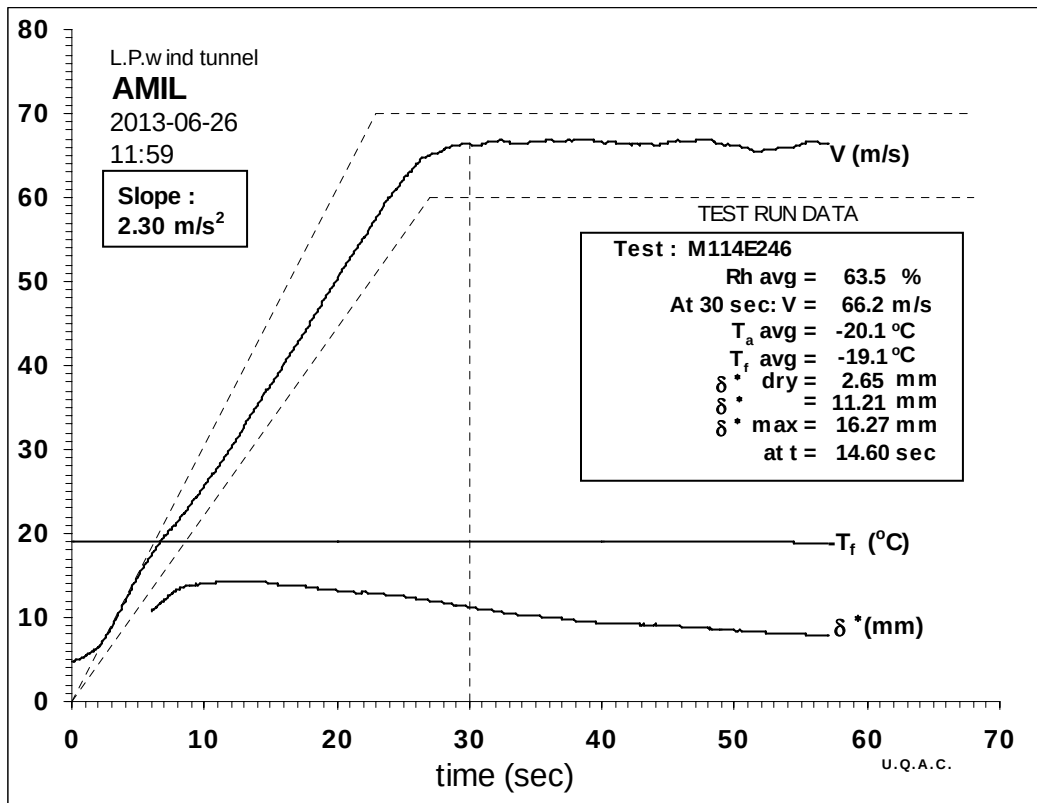

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-20.7	-19.2	61.5	11.81	65.3	2.20	11.76
28	-20.6	-19.1	61.3	12.35	66.7	2.33	11.85
29	-20.5	-19.2	61.7	11.88	65.5	2.13	11.51
30	-20.4	-19.2	61.8	12.14	66.2	2.03	11.02
31	-20.4	-19.2	61.9	12.48	67.1	2.14	11.17
32	-20.3	-19.1	62.0	12.09	66.1	1.94	10.73
33	-20.2	-19.1	62.8	11.99	65.8	1.83	10.40


Averages between 27 and 33 seconds:

30	-20.4	-19.1	61.8	12.14	66.2	2.09	11.21
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114F238

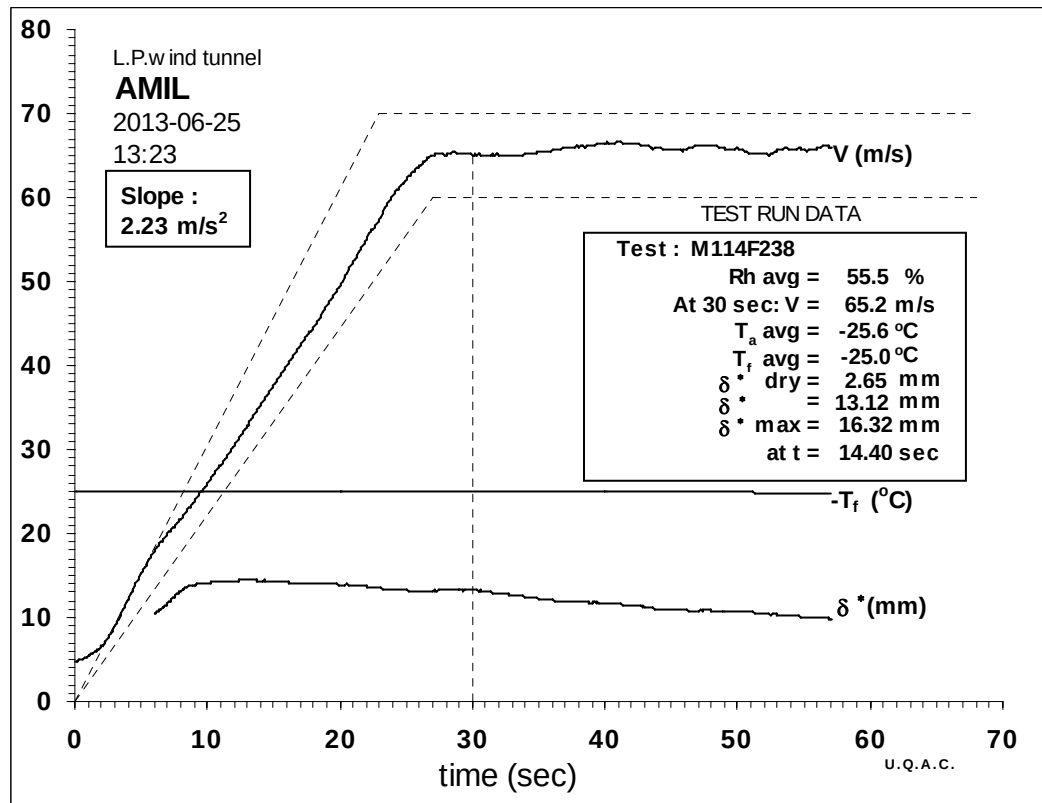

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-26.2	-25.0	53.5	12.08	65.3	2.56	12.74
28	-26.2	-25.0	53.8	12.19	65.6	2.72	13.19
29	-26.1	-25.0	53.7	12.02	65.1	2.74	13.38
30	-26.0	-25.0	54.0	12.10	65.4	2.80	13.53
31	-25.9	-25.0	53.9	12.06	65.3	2.56	12.76
32	-25.8	-25.0	53.8	11.95	65.0	2.58	12.92
33	-25.7	-25.0	54.1	11.65	64.2	2.57	13.11


Averages between 27 and 33 seconds:

30	-26.0	-25.0	53.8	12.03	65.2	2.66	13.12
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114F239

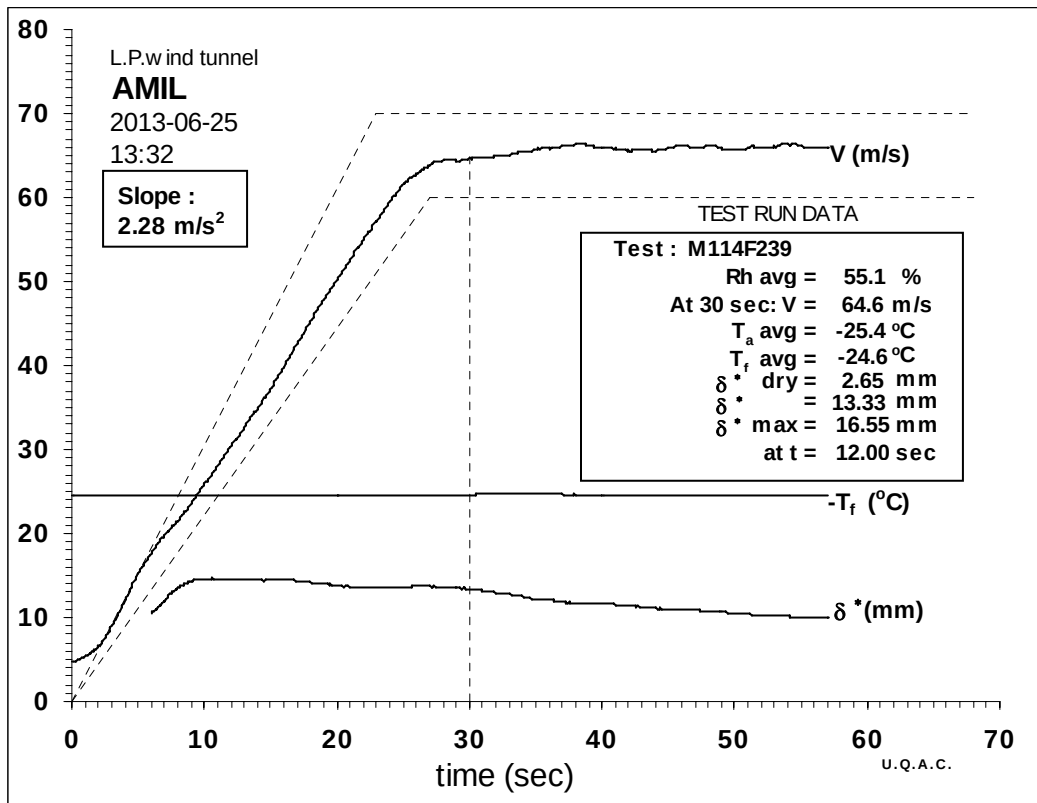

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-26.0	-24.6	53.2	11.79	64.5	2.56	12.97
28	-26.0	-24.6	53.2	11.43	63.5	2.76	13.87
29	-25.8	-24.6	52.9	12.12	65.4	2.82	13.54
30	-25.7	-24.6	53.4	11.82	64.6	2.67	13.28
31	-25.7	-24.6	53.6	11.65	64.2	2.60	13.20
32	-25.6	-24.6	53.3	11.87	64.8	2.65	13.19
33	-25.5	-24.7	53.6	11.93	65.0	2.55	12.84


Averages between 27 and 33 seconds:

30	-25.8	-24.6	53.3	11.79	64.6	2.67	13.33
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

M114F240

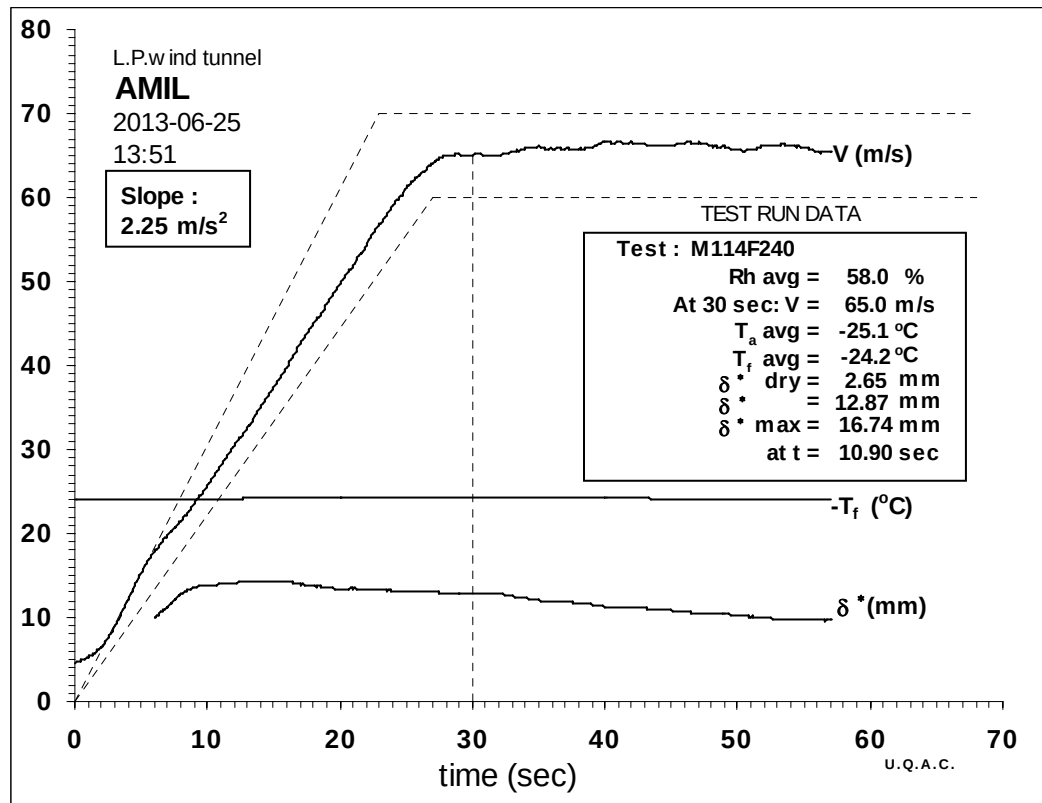

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-25.7	-24.2	55.9	11.87	64.8	2.62	13.05
28	-25.6	-24.2	55.9	11.89	64.8	2.46	12.58
29	-25.6	-24.2	56.2	12.29	65.9	2.70	13.05
30	-25.5	-24.2	56.4	11.84	64.7	2.45	12.56
31	-25.4	-24.2	56.5	11.89	64.9	2.63	13.09
32	-25.3	-24.2	56.5	12.05	65.3	2.58	12.86
33	-25.2	-24.2	56.6	11.70	64.4	2.59	13.11

Averages between 27 and 33 seconds:

30	-25.5	-24.2	56.3	11.95	65.0	2.57	12.87
----	-------	--------------	------	-------	------	------	--------------

Test Duct Dimensions :


S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

This page left blank.

ARCTON LTD. DEICING FLUID

**Arctica DG RTU lot # 28,
Fluid as received J-162**

J162A022

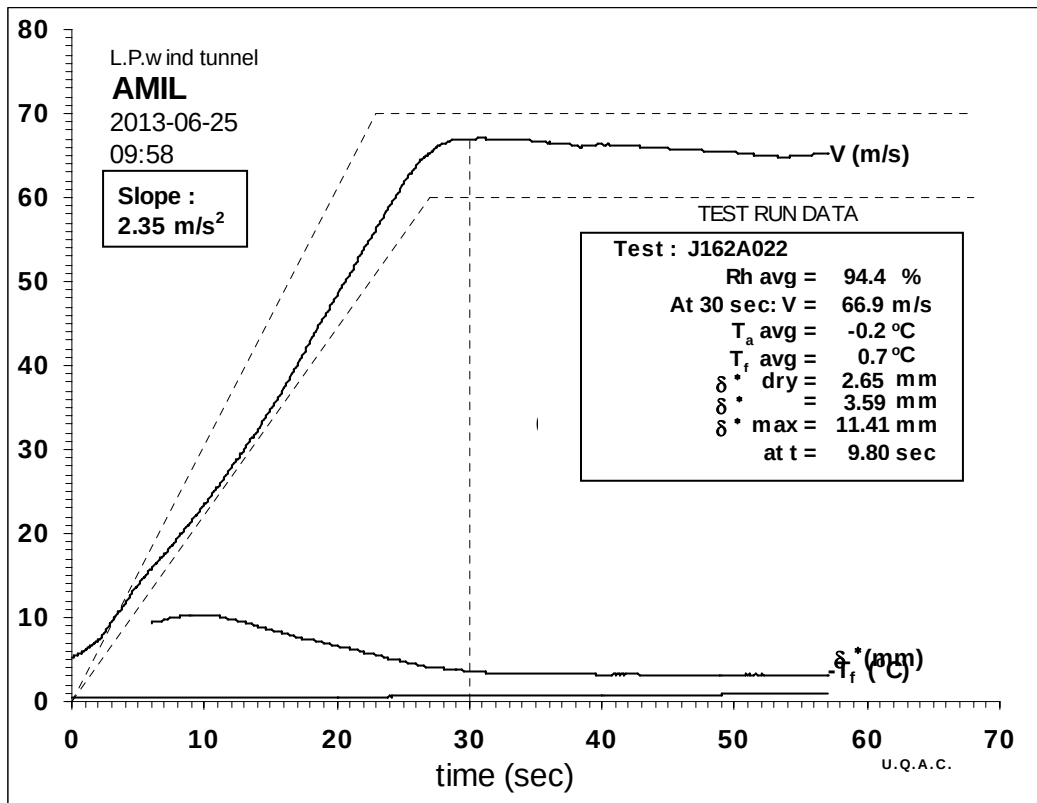

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.4	0.6	93.9	11.24	66.2	0.10	3.86
28	-0.4	0.6	93.6	11.44	66.8	0.07	3.71
29	-0.3	0.7	94.1	11.44	66.8	0.09	3.82
30	-0.3	0.7	93.7	11.66	67.4	0.06	3.67
31	-0.3	0.7	94.1	11.42	66.7	0.01	3.45
32	-0.3	0.7	94.3	11.58	67.2	-0.01	3.39
33	-0.3	0.7	94.6	11.38	66.6	-0.05	3.20


Averages between 27 and 33 seconds:

30	-0.3	0.7	94.0	11.47	66.9	0.04	3.59
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162A023

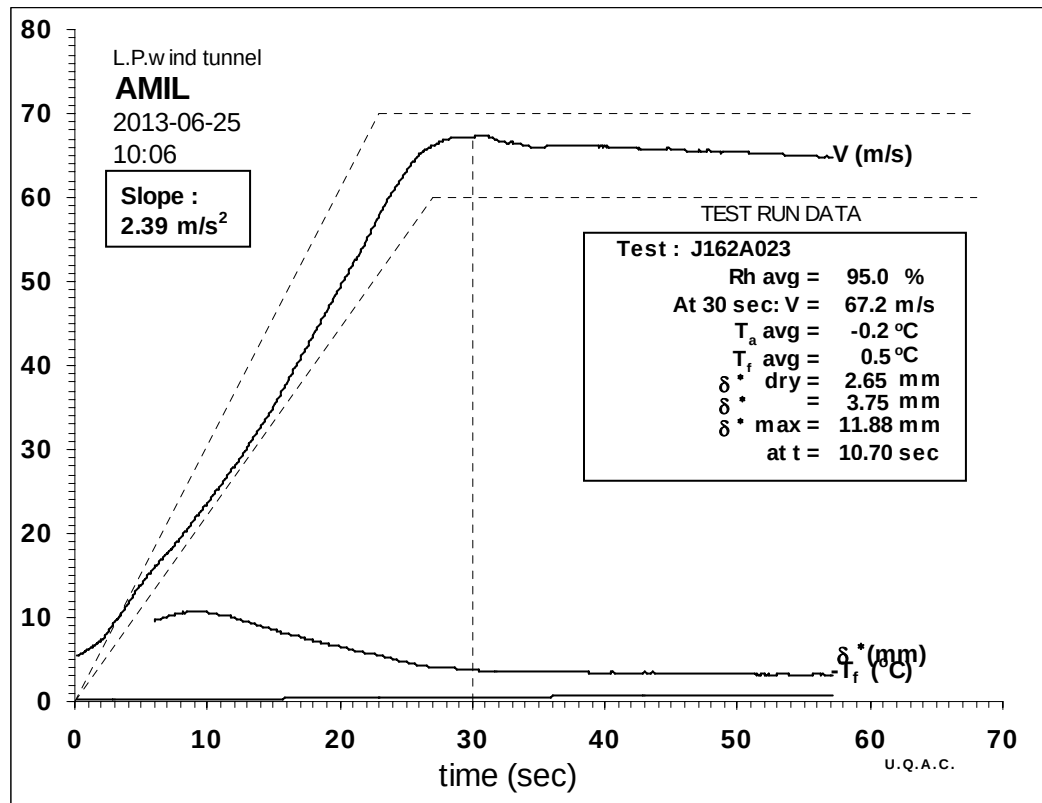

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.3	0.5	94.4	11.32	66.4	0.17	4.19
28	-0.3	0.5	94.2	11.58	67.2	0.14	4.04
29	-0.3	0.5	94.5	11.50	67.0	0.07	3.72
30	-0.3	0.5	94.6	11.82	67.9	0.14	4.02
31	-0.3	0.5	94.6	11.44	66.8	-0.04	3.26
32	-0.3	0.5	95.1	11.78	67.8	0.08	3.74
33	-0.2	0.6	95.3	11.40	66.7	-0.02	3.35


Averages between 27 and 33 seconds:

30	-0.3	0.5	94.6	11.58	67.2	0.08	3.75
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162A024

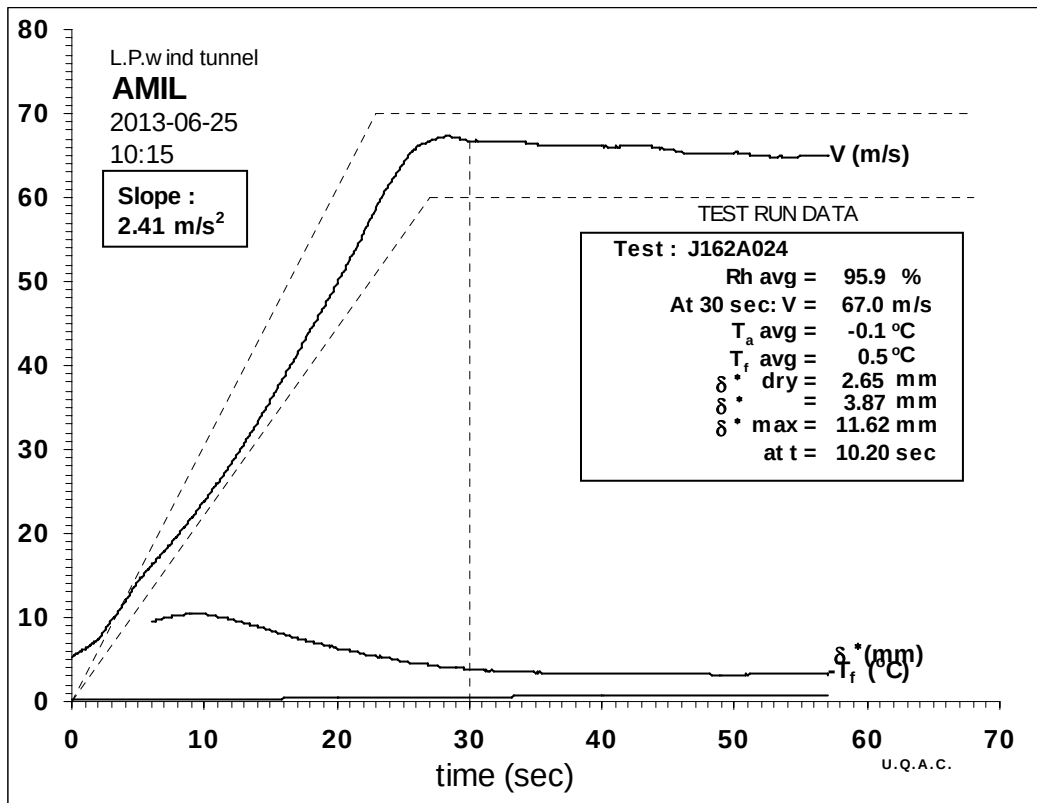

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-0.2	0.5	95.5	11.84	68.0	0.17	4.15
28	-0.2	0.5	95.3	11.63	67.4	0.19	4.26
29	-0.2	0.5	95.5	11.60	67.2	0.13	3.98
30	-0.2	0.6	95.4	11.54	67.1	0.04	3.61
31	-0.2	0.6	95.9	11.16	66.0	0.11	3.91
32	-0.2	0.6	96.3	11.42	66.7	0.02	3.50
33	-0.2	0.6	96.0	11.46	66.8	0.09	3.81


Averages between 27 and 33 seconds:

30	-0.2	0.5	95.7	11.50	67.0	0.10	3.87
----	------	------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162C040

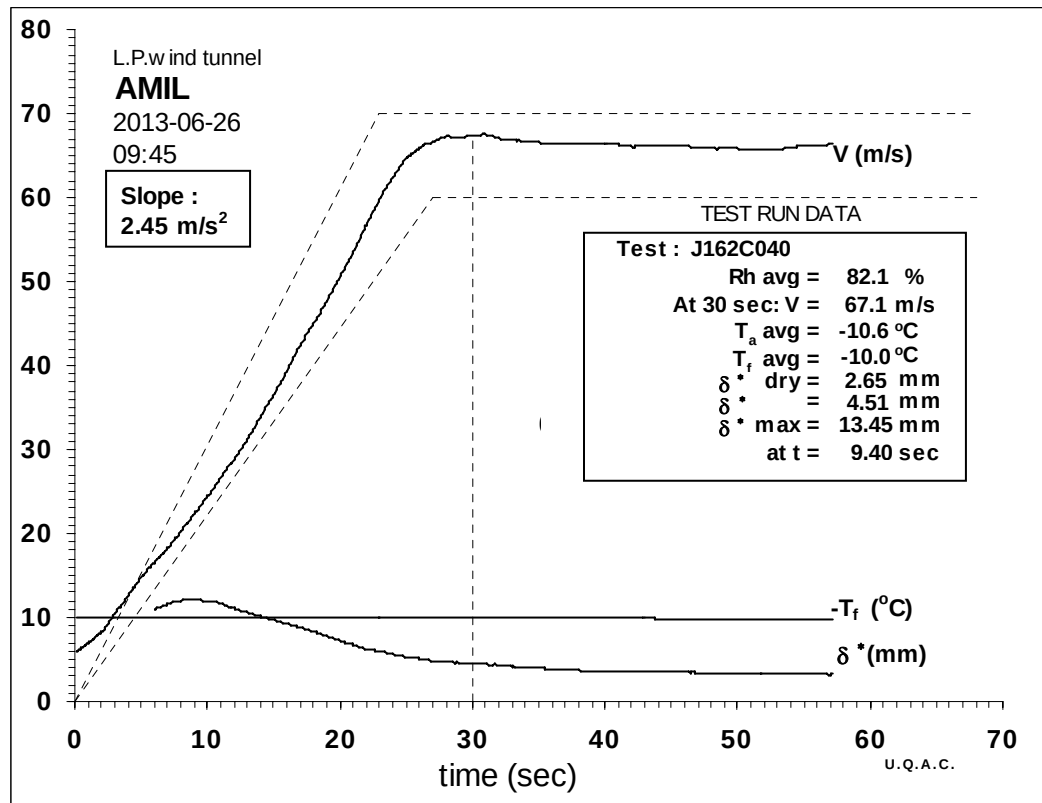

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-10.9	-10.0	80.3	11.78	66.4	0.37	4.99
28	-10.8	-10.0	80.6	11.77	66.4	0.31	4.75
29	-10.8	-10.0	81.3	12.02	67.1	0.27	4.51
30	-10.8	-10.0	81.3	12.28	67.8	0.29	4.61
31	-10.7	-10.0	81.3	12.22	67.7	0.24	4.38
32	-10.7	-10.0	81.6	12.07	67.3	0.18	4.18
33	-10.7	-10.0	82.2	11.77	66.4	0.21	4.30


Averages between 27 and 33 seconds:

30	-10.8	-10.0	81.2	12.02	67.1	0.26	4.51
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

$S_2 = 30802.589 \text{ mm}^2$ $S_3 = 33220.101 \text{ mm}^2$ $B_3 = 301.981 \text{ mm}$ $C_3 = 824.408 \text{ mm}$

J162C041

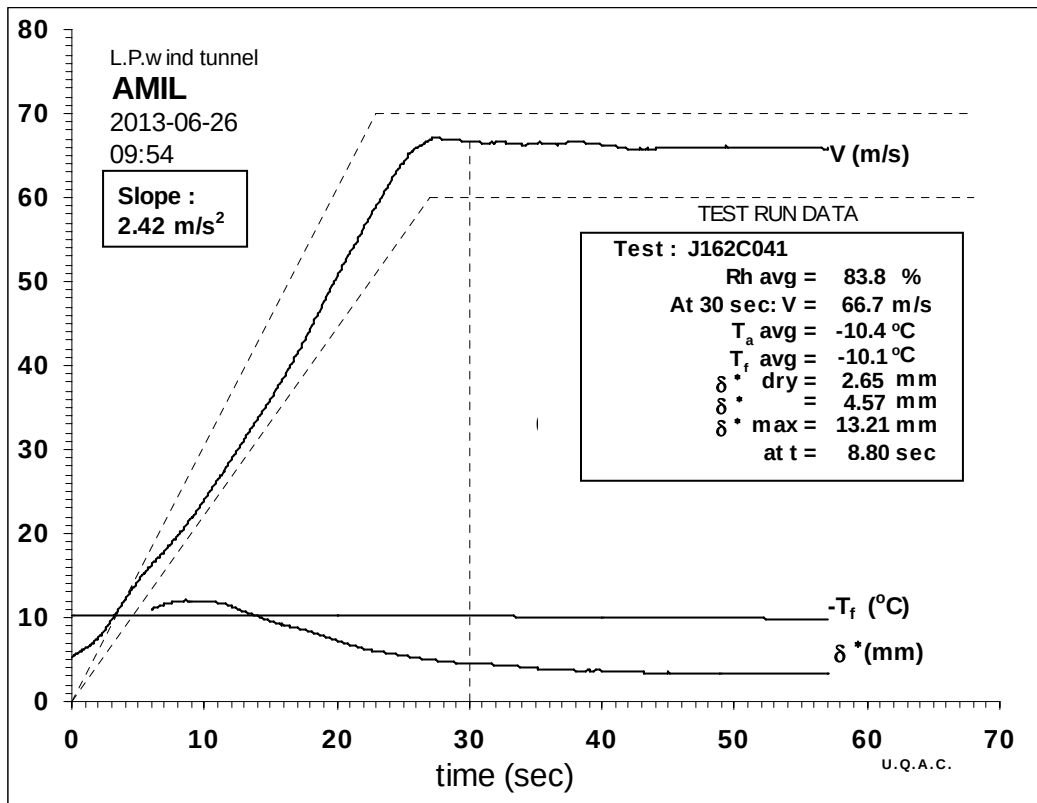

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-10.6	-10.2	82.4	12.28	67.9	0.40	5.04
28	-10.6	-10.2	82.4	11.79	66.5	0.30	4.69
29	-10.5	-10.2	82.8	11.98	67.1	0.28	4.60
30	-10.5	-10.2	83.1	11.83	66.6	0.32	4.75
31	-10.5	-10.2	83.5	11.83	66.6	0.16	4.10
32	-10.5	-10.1	83.2	11.68	66.2	0.23	4.42
33	-10.4	-10.1	83.7	11.65	66.1	0.29	4.67


Averages between 27 and 33 seconds:

30	-10.5	-10.2	83.0	11.84	66.7	0.27	4.57
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162C042

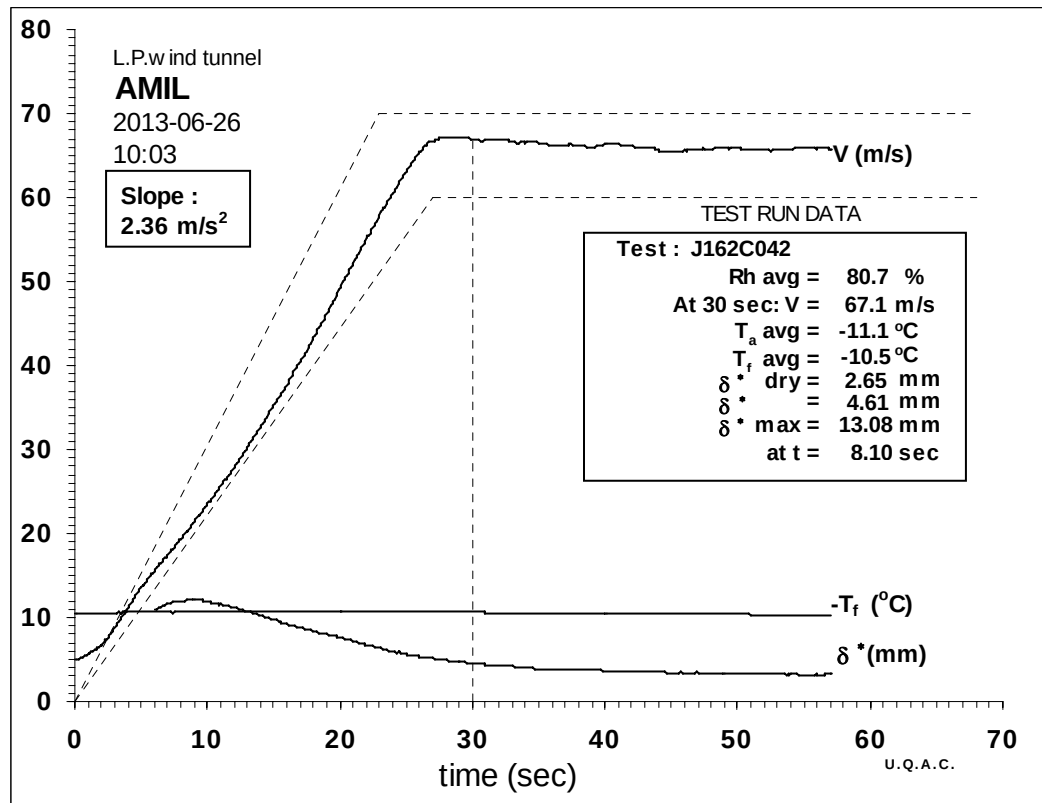

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-11.4	-10.6	78.9	12.04	67.1	0.43	5.19
28	-11.3	-10.6	79.1	12.38	68.1	0.36	4.88
29	-11.3	-10.6	79.1	11.85	66.6	0.33	4.82
30	-11.3	-10.6	79.5	11.96	66.9	0.24	4.44
31	-11.2	-10.6	79.8	12.07	67.2	0.25	4.47
32	-11.2	-10.6	80.1	11.82	66.5	0.22	4.35
33	-11.2	-10.6	80.2	12.02	67.1	0.20	4.23


Averages between 27 and 33 seconds:

30	-11.3	-10.6	79.5	12.02	67.1	0.28	4.61
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162E052

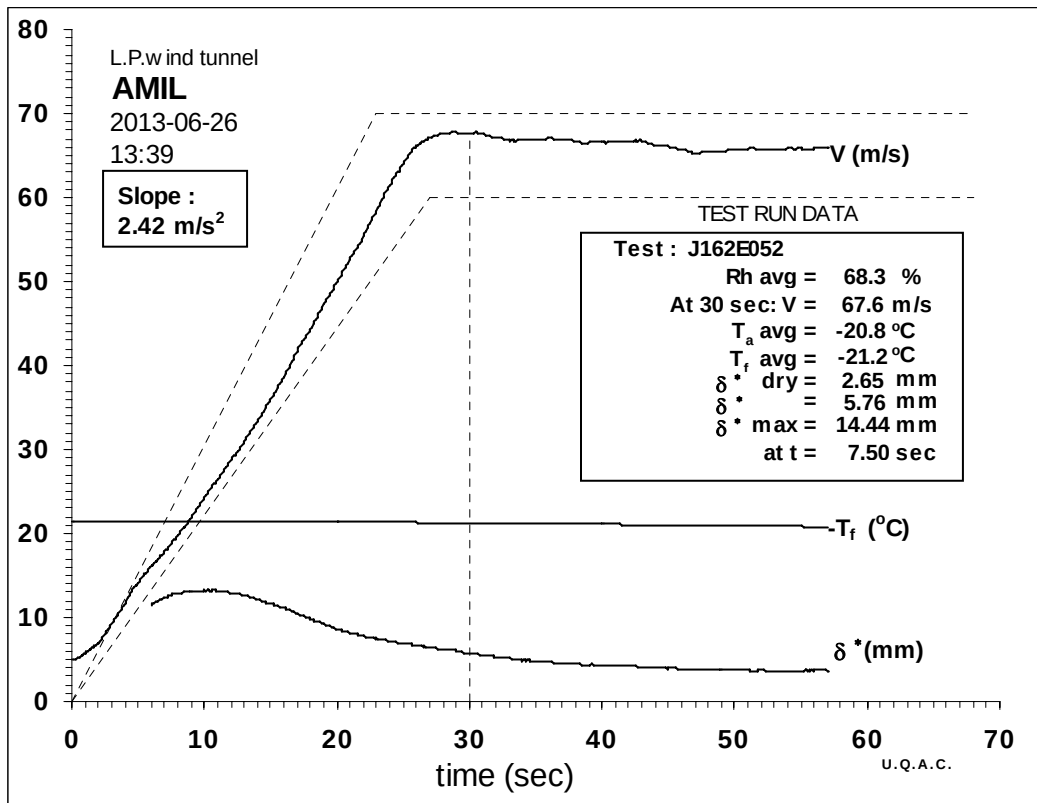

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-21.1	-21.3	66.6	13.17	68.9	0.96	6.94
28	-21.1	-21.3	67.1	12.40	66.8	0.63	5.89
29	-21.1	-21.3	66.8	12.80	67.9	0.73	6.21
30	-21.0	-21.3	66.9	12.69	67.6	0.62	5.82
31	-21.0	-21.3	67.4	12.91	68.2	0.52	5.40
32	-20.9	-21.2	67.5	12.65	67.5	0.52	5.44
33	-20.9	-21.2	67.7	12.25	66.5	0.36	4.86


Averages between 27 and 33 seconds:

30	-21.0	-21.3	67.1	12.69	67.6	0.61	5.76
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162E053

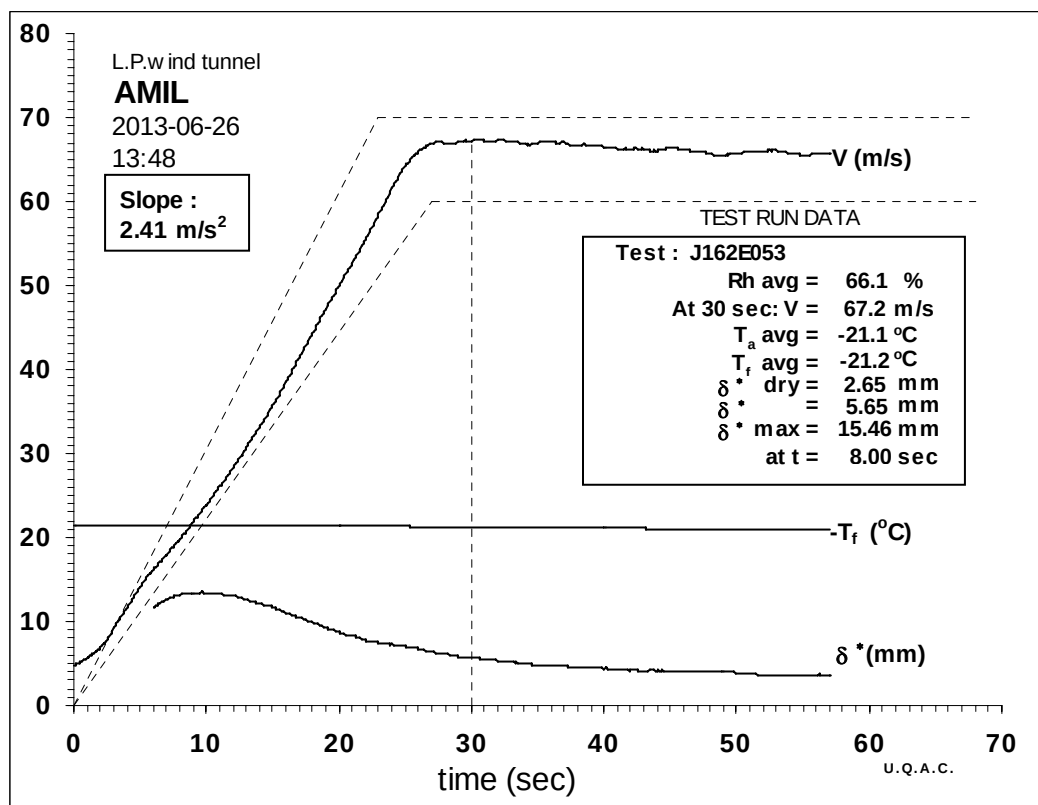

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-21.4	-21.3	64.4	12.43	66.9	0.61	5.84
28	-21.4	-21.3	64.5	12.47	67.0	0.65	5.95
29	-21.3	-21.3	64.7	12.40	66.8	0.60	5.79
30	-21.3	-21.3	64.9	12.32	66.6	0.61	5.85
31	-21.2	-21.2	65.0	13.14	68.8	0.51	5.35
32	-21.2	-21.2	65.0	12.59	67.3	0.51	5.42
33	-21.2	-21.2	65.2	12.18	66.2	0.46	5.28


Averages between 27 and 33 seconds:

30	-21.3	-21.3	64.8	12.53	67.2	0.57	5.65
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162E054

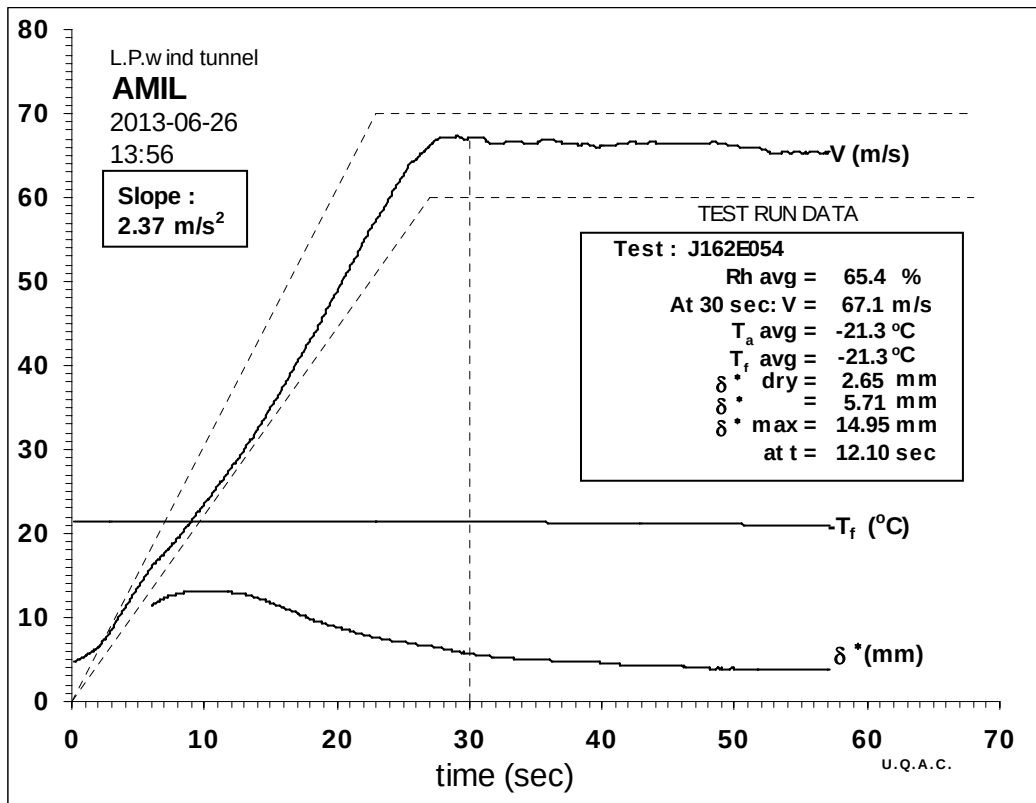

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-21.6	-21.4	64.4	12.89	68.1	0.75	6.26
28	-21.6	-21.4	63.9	12.27	66.4	0.72	6.26
29	-21.6	-21.4	64.0	12.90	68.1	0.67	5.98
30	-21.6	-21.4	64.0	12.59	67.3	0.56	5.61
31	-21.5	-21.4	64.3	12.18	66.2	0.54	5.60
32	-21.5	-21.3	64.6	12.53	67.1	0.40	5.02
33	-21.4	-21.4	65.0	12.32	66.6	0.48	5.35


Averages between 27 and 33 seconds:

30	-21.5	-21.4	64.2	12.51	67.1	0.58	5.71
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162G061

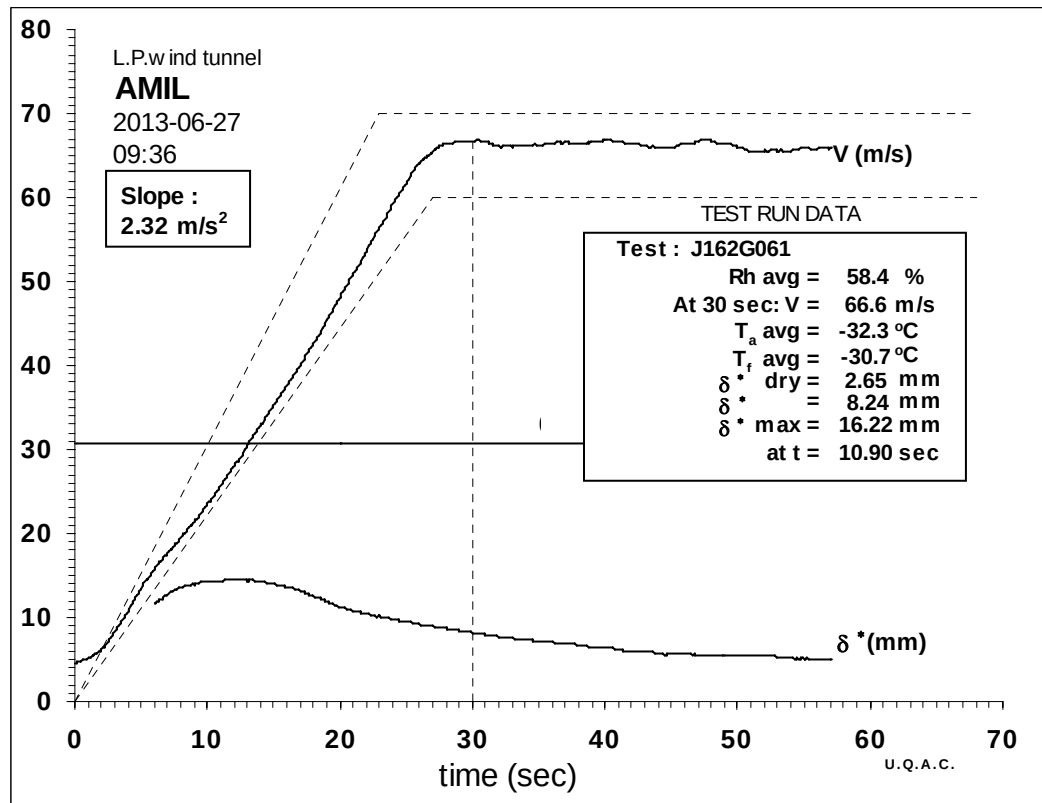

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-32.7	-30.8	57.9	13.06	67.0	1.69	9.44
28	-32.7	-30.8	57.8	12.75	66.2	1.40	8.59
29	-32.6	-30.8	57.7	13.14	67.2	1.34	8.24
30	-32.6	-30.8	58.1	12.96	66.7	1.34	8.31
31	-32.5	-30.8	57.6	12.92	66.6	1.31	8.20
32	-32.5	-30.8	58.0	13.00	66.9	1.13	7.58
33	-32.3	-30.8	57.6	12.42	65.3	1.12	7.75


Averages between 27 and 33 seconds:

30	-32.5	-30.8	57.8	12.91	66.6	1.32	8.24
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162G062

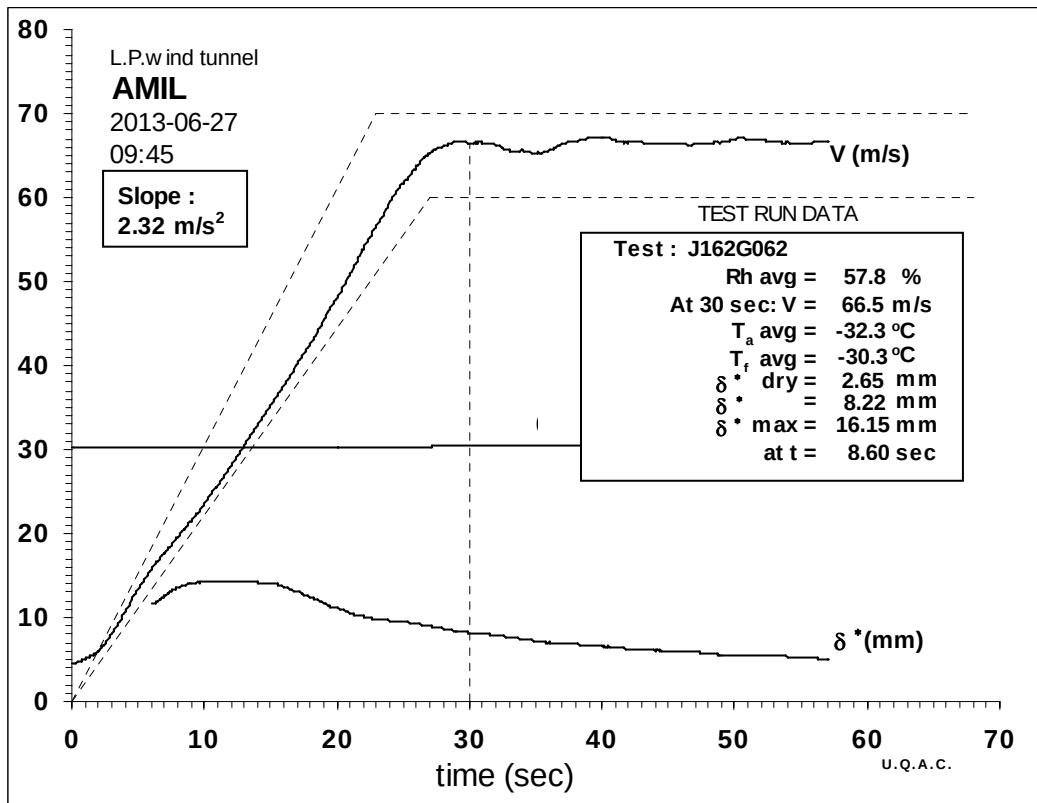

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T _a °C	T _f °C	Rh %	P ₁ -P ₂ "H ₂ O	V m/s	P ₂ -P ₃ "H ₂ O	δ* mm
27	-32.8	-30.3	56.6	12.48	65.5	1.44	8.83
28	-32.8	-30.4	57.1	13.06	67.0	1.44	8.58
29	-32.7	-30.4	57.3	12.87	66.5	1.31	8.25
30	-32.6	-30.4	57.3	12.82	66.4	1.31	8.26
31	-32.5	-30.4	57.2	12.96	66.8	1.21	7.85
32	-32.5	-30.4	57.1	12.88	66.5	1.29	8.17
33	-32.4	-30.4	57.2	12.94	66.7	1.15	7.67


Averages between 27 and 33 seconds:

30	-32.6	-30.4	57.2	12.89	66.5	1.31	8.22
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

J162G063

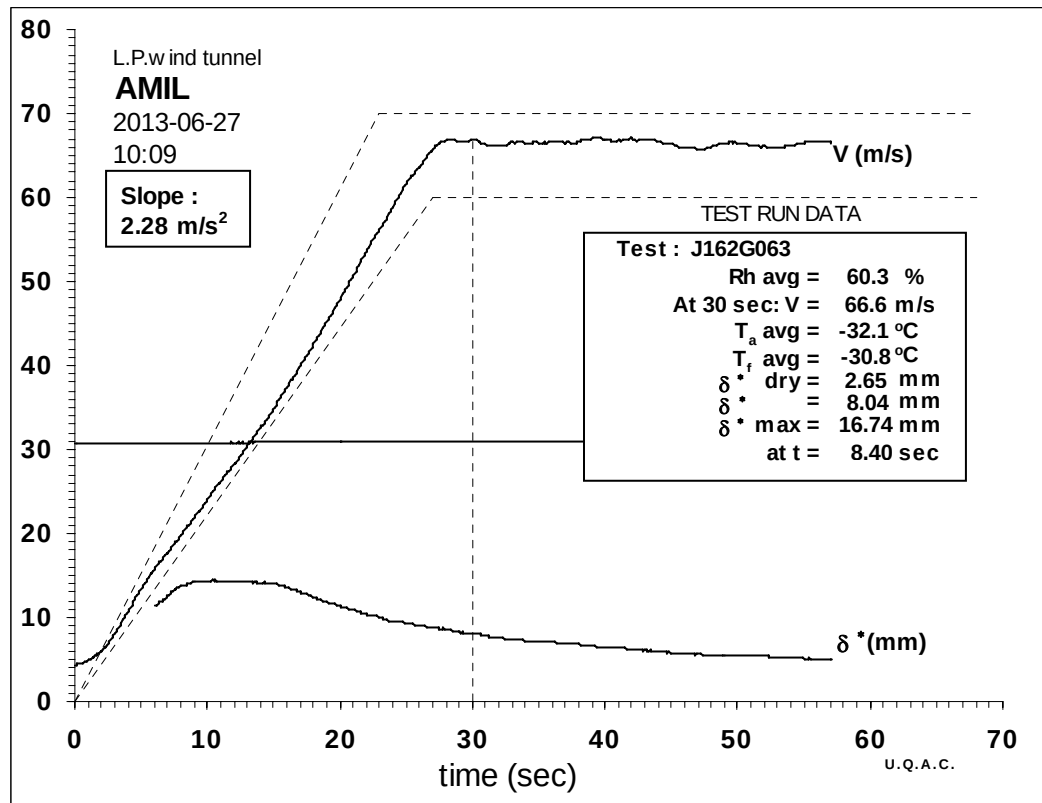

CRITICAL TIME TEST DATA AVERAGED OVER ONE SECOND

time Sec	T_a °C	T_f °C	Rh %	P_1-P_2 "H ₂ O	V m/s	P_2-P_3 "H ₂ O	δ^* mm
27	-32.4	-30.9	59.7	12.78	66.3	1.24	8.04
28	-32.4	-30.9	59.8	13.06	67.0	1.43	8.57
29	-32.4	-30.9	59.6	13.34	67.8	1.45	8.55
30	-32.3	-30.9	59.7	12.88	66.6	1.30	8.20
31	-32.2	-30.9	59.6	12.51	65.6	1.04	7.41
32	-32.1	-30.9	59.6	12.82	66.4	1.21	7.92
33	-32.1	-30.9	59.8	12.60	65.9	1.02	7.32

Averages between 27 and 33 seconds:

30	-32.3	-30.9	59.7	12.88	66.6	1.26	8.04
----	-------	--------------	------	-------	------	------	-------------

Test Duct Dimensions :

S2 = 30802.589 mm² S3 = 33220.101 mm² B3 = 301.981 mm C3 = 824.408 mm

This page left blank.

ACCREDITATION

This page left blank.



In accordance with PRI Program Document AC3001, Audit Criteria for compliance to SAE AMS 1424 and AMS 1428:

Anti-Icing Materials International Laboratory (AMIL)

Universite du Quebec a Chicoutimi
Department des Sciences Appliquees
555, Boulevard de l'Universite
Chicoutimi Quebec, Canada G7H 2B1

Has had its facilities examined and approved through continuing audit procedures as established by the Commercial Aviation Accreditation conformance to the applicable specification requirements for the Aircraft Ground Deicing/Anti-Icing Aerodynamic acceptance test facilities.

This certificate is granted by authority of the Performance Review Institute for:

Testing of Deicing/Anti-Icing Fluids

Certificate Number: 0001 – C
Expiration Date: 31 October 2017
Issue Date: 13 September 2012

Joseph G. Pinto, Vice President and Chief Operating Officer

Performance Review Institute (PRI) 161 Thorn Hill Road Warrendale, PA 15086-7527